

Report

Project title	Recyclability of packaging Assessment catalogue
Principal	Interzero Recycling Alliance GmbH
Project-No.	530592
Editor	Thorsten Pitschke
Valid as of	January 2025

TABLE OF CONTENTS

1	Initiative.....	1
2	Key aspects of the assessment methodology.....	2
3	Target processes for mechanical recycling of packaging.....	4
4	Overview of assessment catalogue	15
5	Level 1: Allocation of the packaging to the collection system.....	18
6	Level 2: Sorting capacity of mixed packaging (LWP) collected.....	20
7	Level 3: Suitability for mechanical recycling and provision of secondary products	29
8	Quantitative recyclability assessment	51
	Literature	56

1 Initiative

For the purposes of encouraging recycling-friendly packaging design, discussions between the stakeholders in the value chain are essential. Platforms and offers for exchange already exist, some of which are exclusive, however. There is a wide-ranging need for further information on the requirements regarding recycling-friendly packaging design among developers, bottlers and the retail trade, though. In this respect, Section 21 of the German Packaging Act, which envisages the structuring of licence fees for sales packaging according to recyclability, offers a strong potential for steering. Through the ecological design of the licence fees, recyclable packaging should, in principle, be subject to low participation fees, while non-recyclable packaging should be subject to higher participation fees. Section 21 of the German Packaging Act addresses the question of a specific assessment of packaging recyclability in terms of the stakeholders who are involved in the life cycle of a piece of packaging. In the following, the key framework conditions for a methodology to determine the recyclability of packaging are presented. The starting point for the related considerations are, among others, the waste management regulations on the disposal of packaging, the Circular Economy Act as well as the German Packaging Act and the Packaging Ordinance in their currently valid versions. In addition to this, the framework which is formulated in DIN EN 13430, “Requirements of packaging regarding material recycling”, is also taken into account.

In the scope of the update which took place in September 2024, the assessment catalogue was adapted to the current version of the minimum standards of the Central Agency Packaging Register [ZSVR 2024].

The goal of recycling is to reduce the use of raw materials and energy in the production of new products through the use of recycled materials. The term recyclability basically refers to the attribute of a product which allows the materials that are used to be returned to the material cycle at the end of their life cycle, thereby closing the material loop. In this context, the degree of recyclability depends on

- how the packaging is designed and configured,
- the quality and quantity in which the packaging can be made available to the material-specific recycling methods and processed accordingly
- which sorting and recycling techniques are used by the waste management industry to separate the individual material streams and concentrate them into target fractions with a high yield, and
- the level of quality that the recycled product achieves, in the knowledge that reuse as a substitute for the primary material is the pursued objective

2 Key aspects of the assessment methodology

2.1 Research subject

According to the definition in the German Packaging Act and DIN 55405 “Packaging - Terminology - Terms and definitions”, packaging is a product for the storage, protection, handling, delivery or presentation of goods which is passed by the manufacturer onto the user or the consumer.

The focus of this recyclability assessment concept is on sales packaging. Sales packaging typically accumulates with the end user after use, and is then collected via collection systems of the dual systems or, in the case of beverage packaging with a mandatory deposit, through the deposit system of the retailer. The packaging materials generally used, also referred to as packaging substances, are: glass, plastics, paper/board/cardboard (PBC), aluminium, tinplate and combinations or composites of these materials (for example, liquid packaging board). Several materials are often used in the packaging, some only in small shares. As regards the assessment, packaging aids such as labels or closures are also considered part of the packaging.

2.2 The distinction between recyclability/eco-design

For manufacturers and developers of packaging, the recyclability is, among other factors, a factor in the overall context of the “eco-design” of packaging. Other aspects discussed in this context include, for example:

- Eco-balance as a method for systematising and assessing environmental impacts over the entire life cycle of packaging. In this respect, the statement on the environmental impact is always a question of the systemic limits of the consideration. The consideration starts with the extraction of raw materials and can extend to the reuse as a recyclate in the production of new packaging or the additional consideration of the packaged goods.
- Material efficiency as a strategy for reducing the consumption of materials: the same result is to be achieved with fewer materials. The steps for achieving this range from material-saving manufacturing processes to improved product design, from staff training, through to cooperation with suppliers and customers. Material efficiency is primarily an issue in the manufacturing process, and not in the recycling process after the end of the use.
- Recycled content as a benchmark for the share of secondary materials in the new product. Working towards a (high) share of secondary materials is a step which encourages the closing of material cycles.

The aforementioned aspects of the eco-design of packaging can relate to different life cycle stages, which means goal-related conflicts between these dimensions are also possible. Within the framework of this concept, only the recyclability of a piece of packaging is assessed; conclusions on the further dimensions of eco-design cannot be drawn from this assessment.

2.3 Recyclability assessment

The determination of recyclability must take place in relation to an underlying recycling structure (for example, the collection, sorting and recycling processes that are used). In this respect, the recycling method (i.e. mechanical, raw-material-based and/or for energy recovery) and the quality of the respective recycling products in terms of the potential areas of reuse are especially relevant.

In encouraging mechanical recycling¹, the German Packaging Act (Section 21 [4]) provides the reference point to which the recyclability of packaging should make reference. Accordingly, in terms of the methodology presented, packaging which, after its collection and sorting,

- can be recycled mechanically to a high-quality, is considered to be **recyclable**.
On this basis, mechanical recycling into products which replace the primary materials originally used is referred to as high-quality. The availability of the high-quality treatment capacities as well as the extent of the high-quality mechanical recycling is taken into account in the assessment.
- can only be recycled for the purpose of energy recovery, is considered **non-recyclable**.

The recyclability assessment also includes the aspect that the success of the mechanical recycling in terms of the existing recycling streams should not be placed at risk in terms of the quality and yield, due to the introduction of impurities, for example. Unwanted substances, materials or material combinations are to be identified during the assessment and assessed in terms of the possibility of their removal and their influence on the product quality.

The objective of the recyclability assessment is, on an efficient and valid basis, to determine the potential on whether and to what extent a piece of packaging or the materials or material combinations to be separated from it fulfil the respective physical or chemical requirements to remain in the path for high-quality mechanical recycling during the sorting and recovery processes.

In this context, a practical test to be carried out specifically for each piece of packaging at actual recycling plants to quantify the actual recyclability is not envisaged. The examination of the physical or chemical prerequisites of the characteristics is usually carried out on the basis of product information and experimental research.

2.4 Limits of the consideration

In principle, the recyclability assessment covers the entire waste management chain concerning the packaging following the end of use. These steps are:

- **Collection**
The delivery of the used packaging to the respective material-specific collection system (including possible separation by the consumer into packaging materials, capacity to be completely emptied, assessment of incorrect allocation to the collection system, etc.)

-

¹ According to the German Packaging Act, mechanical recycling is recycling with processes in which new material of the same substance is replaced or the material remains available for further material use

- **Sorting**
The sorting of collected mixed packaging
- **Preparation**
The material-specific, mechanical recycling of the packaging materials and the provision of a secondary product (for example, re-granulate)

During every stage of the recycling chain, the removal of packaging components can take place which are either unsuitable for high-quality mechanical recycling or do not apply to this path. With respect to the methodology to be developed in this case, recyclability is therefore to be understood as a gradual characteristic which ultimately assesses the relationship between the expected quantity of the secondary product and the quantity of the packaging material used.

The consideration of the individual process steps and products of the mechanical recycling is of importance to the recyclability assessment. Simply making a piece of packaging available for a high-quality mechanical recycling process as an indicator of its recyclability while calculating the recycling quotas, would fall short.

2.5 Status of the referenced waste management structure

The recyclability assessment is based on DIN EN 13430 (Packaging – Requirements for packaging recoverable by material recycling) on the basis of the collection and recycling processes which are relevant and used at the industrial level in Germany today (status quo). A more detailed description of the material-specific recycling processes is provided in Section 3.

-

2.6 Summary

The recyclability assessment for a piece of packaging characterises the share of materials contained in the packaging which can be reused to manufacture products from the original primary material subsequent to the sorting and recycling. Accordingly, to determine the expected recyclability, the chemical and physical suitability of the packaging is assessed in terms of its sorting capacity and recyclability. The reference point for this assessment is provided by the sorting and recycling processes specific to packaging materials which are relevant and used at industrial level in Germany.

3 Target processes for mechanical recycling of packaging

After its use, sales packaging is collected separately from residual waste on a material-specific basis via the collection systems or, in the case of beverage packaging with a mandatory deposit, through the deposit system of the retailer.

In this respect, consumer behaviour and the basic manageability of the packaging during the separate collection must firstly be taken into account. One example of this is the possibility for the allocation to the collection system on the part of the consumer. This takes place as soon as the waste packaging can be clearly allocated to the collection system created for it. Container glass, for example, can be classified as clearly sortable, as the material of glass is clearly

recognisable as such to the consumer. The same applies to the allocation of metallic packaging to the respective separate collection systems (if available). This can also be assumed to be the case for the unambiguously correct allocation of plastic sales packaging to the designated collection methods (yellow bag, yellow bin). It becomes more difficult when the packaging consists of different materials that the consumer has to separate into individual components (for example, yogurt cups: aluminium lid, thin plastic container with a cardboard sleeve). The consumer is required to make his or her personal contribution to the correct technical sorting process. Not all consumers are prepared to do this, which is why losses in the individual packaging components can be expected here as well.

The following illustration of the preparation chains for the various packaging waste shares describes a wide-ranging non-exclusive state of the art. In general, the processes and process chains presented provide the procedural framework for the recyclability assessment, i.e. the visual and physicochemical treatment processes that are presented are used in order to assess the recyclability.

Process-based innovations in the preparation sector may make it necessary to adapt the described state of the art in the future

3.1 Sorting of mixed LVP

Lightweight packaging (LVP), i.e. sales packaging made of plastic, aluminium, tinplate and composite materials such as liquid cartons, is usually collected in a mixture. Collection is mainly carried out in the collection system. The mixed packaging is then separated in sorting plants into fractions for downstream recycling. The sorting result is influenced by contractual and legal requirements as well as by factors that can be attributed to the technical design of the sorting plant and its mode of operation. The state of the art of WEEE sorting is characterised by a highly automated process design and the separation of plastic packaging by type of plastic. Depending on the specific system configuration, the following sorting fractions are produced during state-of-the-art LVP sorting: plastic films (predominantly LDPE), PE, PP, PS, PET, MPO (mixed polyolefins), PO-flex, PP-flex, mixed plastics (MKS) and PPK from LVP, liquid cartons (LPB), ferrous metals such as tinplate and non-ferrous metals such as aluminium.

The main steps of sorting the LVP collection mix according to the state of the art are shown in Figure 3 1 (see also [UBA 2024]):

- Opening of the containers (yellow bag) to expose the packaging waste
- Screen classification as preparation for the size-dependent sorting stages and for separating small-sized sorting residues (<20 mm)
- Wind sifting of fractions >220 mm and 20 - 220 mm to separate plastic films or a fraction of flexible mixed plastics (MKS). The film fraction is often additionally separated by type

of plastic using near-infrared (NIR) separators or integrated processing. In this way, the purest possible **LDPE fractions** or fractions with **flexible PO/PP** are produced.

- Magnetic separation for the recovery of **tinplate** or **ferrous metals**
- Separation of **liquid packaging board (LPB)** using NIR from the 20 - 220 mm fraction (heavy and light windage fraction) and the partial stream from eddy current separation
- Eddy current separation for the extraction of **aluminium**
- Multiple sorting of rigid plastics using NIR. As a rule, **PET, PE, PP**, often **PS**, sometimes **MPO** and a **PBC** fraction are produced from plastic types.

Manual inspection of the automatically separated sorting fractions. (AI)-supported object recognition in combination with NIR separators or sorting robots are already in use in some plants as an alternative or supplement to manual sorting (see [UBA 2024]).

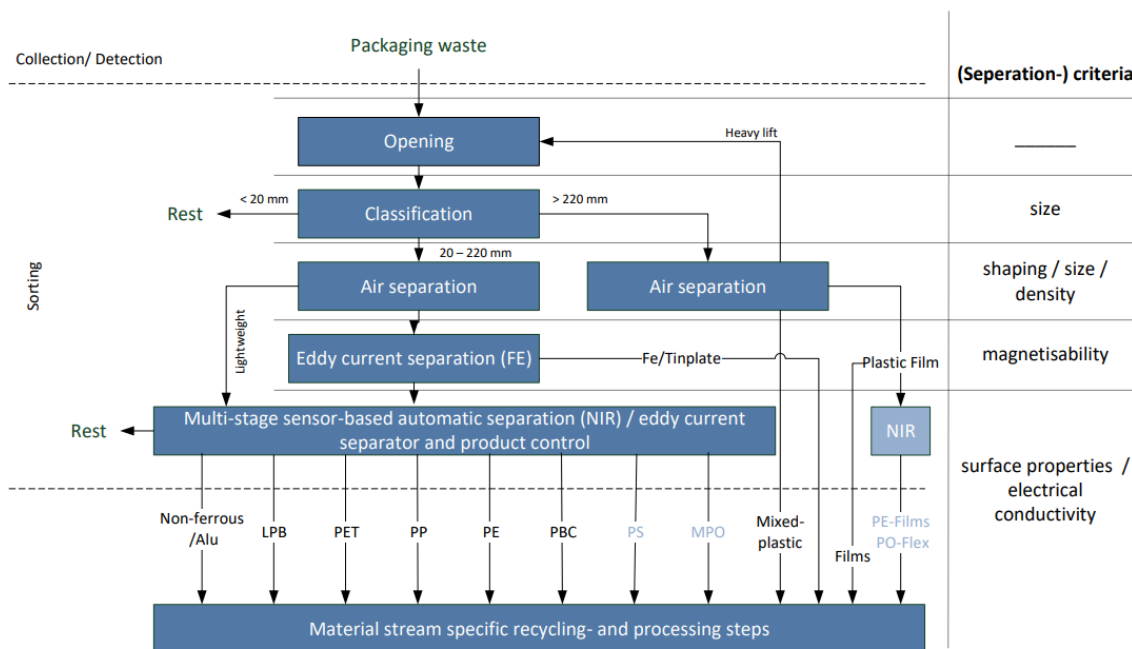


Figure 3-1: Process steps for sorting LWP Blue text: Fractions are partially produced, i.e. in some sorting plants.

The quality requirements for these fractions (product specifications) are set out in a catalogue shared by the system operators². The typical sorting fractions are:

- Plastics: PP, PE, PET (transparent bottles), films > DIN A4, MKS and large plastic hollow bodies. In some cases, the fractions PS, PE films, PO-flex or PP-flex, black dimensionally stable plastics and PET trays are also produced
- Metals: aluminium, tinplate
- Fibre-containing fractions: Liquid cartons, partly PPK composites
- Other: sorting residues

² For detailed information, see <https://www.gruener-punkt.de/de/download.html>

3.2 PE, PP, PS and films

When it comes to recycling packaging plastics, the focus is on thermoplastics. Thermoplastics can be moulded within certain temperature ranges. Provided that the material is not overheated and therefore damaged, this process can be repeated to a certain extent. The number of possible repetitions essentially depends on the quality, i.e. purity, of the material flow. Among thermoplastics, the polyolefins PP and PE are used particularly frequently in the packaging sector. The recycling of plastic packaging made of PP, PE and PS essentially involves the steps shown in Figure 3-2.

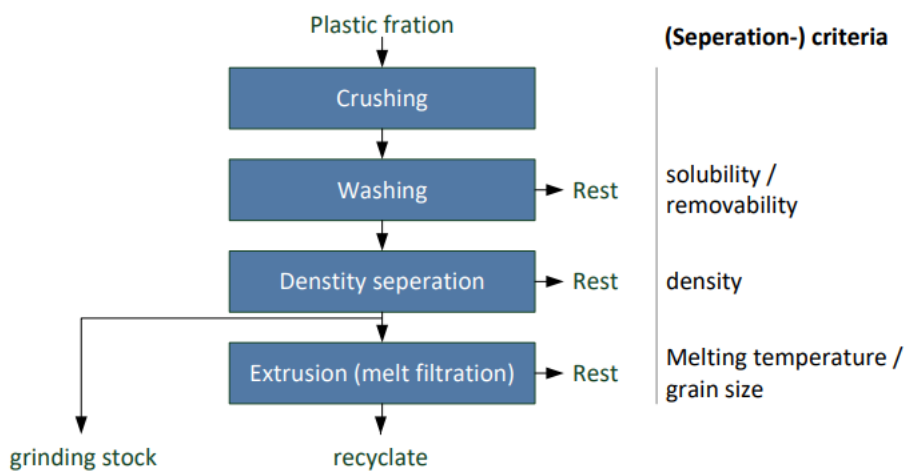


Figure 3-2: Process steps for the recycling of standard packaging plastics

The PP, PE and PS sorting fractions have a purity of at least 94%. The first step in the recycling process, after opening the bales, is to shred the plastic packaging. During the subsequent intensive washing process, any remaining filling material, adhesions, labels etc. should be removed as far as possible. In most systems, the washing is carried out cold [UBA 2024] and no washing substances are usually added. Material composites that cannot be dissolved in the washing process can lead to challenges in the subsequent process steps. Some systems improve the quality of the cleaning by hot washing and thus increase the recyclate quality [UBA 2024].

In a subsequent density separation in the float and sink process, the target plastic (float fraction for PE or PP recycling and/or sink fraction for PS recycling with 2-stage density separation) and the impurities are removed to further increase the purity of the polymer fraction. However, this has its limits if materials with very similar densities are to be separated from each other or if adhesions (for example, multilayers or PBC residues) on the target polymer change its original density.

The main processing step from PE and PP regrind to recyclate is extrusion, including melt filtration. The material is melted, homogenised, degassed and filtered in the extruder. Some plants sort the regrind by colour or material before melt filtration [UBA 2024]. According to [UBA 2024], PS is dried after density separation and usually discharged as regrind.

Plastic films > DIN A4 are separated in the sorting process via classification and air separation. Many systems also sort small-format films < DIN A4 using NIR separators. The films separated

in this way are predominantly made of LDPE. The films are shredded into regrind. According to [UBA 2024], PP components and other impurities are separated in some plants using NIR. During the subsequent washing process, usually cold and without detergents, adhesive residues, paper and labels and other impurities are removed. Density separation is then used to remove components with a density >1g/cm³. The regrind is then dried and homogenised in the extruder, melted and processed into regranulate.

3.3 PET

In the case of PET, there are high demands on the recycling process and the quality of the secondary products, as the recycled pellets produced are often reused in the packaging sector. PET recycling is currently focussed on transparent PET bottles from the deposit system or the LVP sorting. Only a small amount of rigid PET packaging, such as trays or trays from German packaging collections, is currently recycled.

Figure 3-3 shows the main steps in the recycling process.

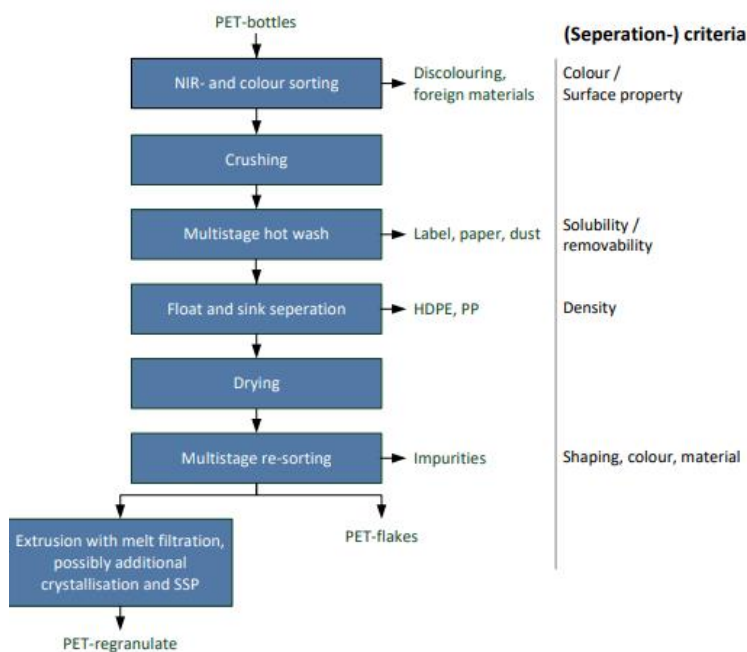


Figure 3-3: Process steps PET recycling (according to [UBA 2024]).

According to [UBA 2024], PET multilayer trays and opaque PET trays are separated in advance using NIR-VIS and sometimes also manually. After pre-sorting and, in some cases, colour sorting, the collected PET bottles are crushed into flakes and cleaned of labels, beverage residues and other dirt particles in several stages using hot water and caustic solution. Caps, etc. are discharged as part of a float-sink separation process. The closure material (PE, PP) is usually recycled. The PET flakes remain in the sink fraction due to their higher density. The flakes are then dried. In order to further reduce the proportion of impurities, the flakes then undergo further sorting steps such as air separation, material and colour identification and metal separation.

Today, recyclers generally sell the flakes as regrind. Only a few recyclers produce recycled pellets themselves through melt filtration. Very occasionally, SSP (solid state polymerisation) is integrated directly into the recycling process to improve the quality of the recycled pellets (see [UBA 2024]).

One of the challenges in melt filtration of PET is that, due to the high melting temperature of PET, organic impurities are carried over into the recyclate and significantly reduce its quality. PA copolymers, for example, are carried into the product and can lead to a yellowish colouration of the recyclate, which can then only be used for the production of coloured bottles.

3.4 Mixed plastics (MP)

MP is often made available for energy recovery after sorting. In some cases, however, MP is also sent for processing into intermediate plastic products (e.g. recycled pellets). If the MP is recycled in this way, the basic process steps of wet mechanical plastics recycling (shredding, washing, density separation and extrusion; see also Figure 3-4) apply, whereby the product requirements are generally less demanding compared to regranulate made from plastic types. However, FMDs are also converted directly into finished products (e.g. noise barriers, fence bases) in dry processes, for example via intrusion processes, although this does not usually replace the use of primary plastics³. The fine-grained mixed plastics are further processed into products in intrusion processes after agglomeration with the addition of colourants and/or film agglomerates [Bosewitz, 2013].

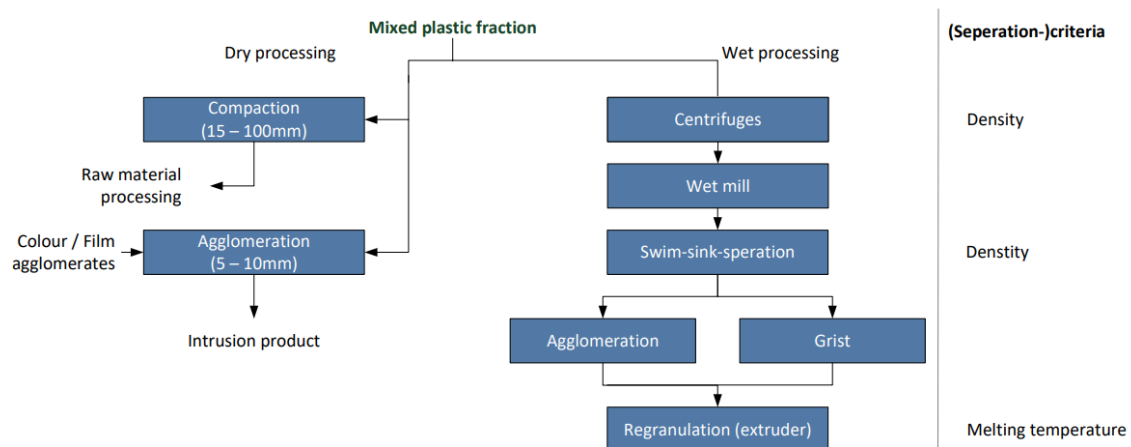


Figure 3-4: Overview of the processing paths of mixed plastics [Bosewitz, 2013].

3.5 Liquid packaging board (LPB) and PBC from LVP (PBC composites)

LPB is required to have a purity of at least 90 % after sorting. The aim of processing LPB is to recover the cellulose fibres as well as the plastic-aluminium components. The prerequisite for this is that the plastic-aluminium content can be gently separated from the cardboard.

³ According to [Consultic 2015], around 60% of materially recycled FMD can be found in such products.

An essential part of LPB recycling is the washing process, in which the fibres are separated from the aluminium and plastic components. To do this, the material is first shredded and then fed into a large, approx. 30 metre long washing drum. With the addition of water, the mixture is defibred in the rotating drum. At the end of the drum, the fibre pulp is flushed out through small openings, separating it from the film residues with the aluminium content. The fibre pulp is cleaned of foreign matter in cleaning stages and then, after thickening and drying, fed to the processing lines for further paper production. The reject, consisting of the foil-aluminium portion, can be used for energy recovery in cement plants or for material recycling in special recycling plants. LDPE regranulate or PO regrind and aluminium concentrate are currently produced as part of mechanical recycling (see [UBA 2024]).

Figure 3-5 shows the main steps in the recycling of LPB

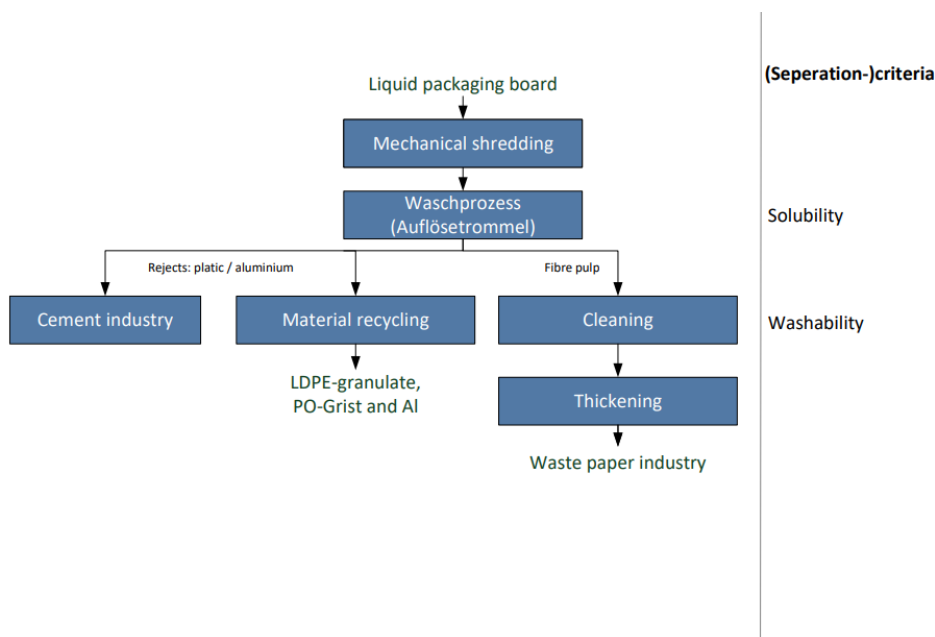


Figure 3-5: Process steps liquid packaging board recycling

When recycling the PBC fraction of LWP, which is rich in composites, the process steps are similar to those for recycling the LPB fraction. The aim is to recover the fibre content. The main process step is also a washing process with appropriate residence times to separate the composites. Components that cannot be separated are discharged as rejects and are usually sent for thermal recycling.

3.6 Aluminium

Aluminium in the LWP fraction is often found in films and composite packaging. Pyrolysis has become established for the recycling of aluminium from the LWP collection. Figure 3-6 shows the main steps of the process (see [GDA, W 18] and [Erdmann et al. 2009]):

- Crushing
- Removal of impurities via magnetic / eddy current as well as float and sink separators
- Pyrolysis (rotary kiln pyrolysis with downstream bench annealing) for the removal of organic impurities

- Post-sorting and sensor-assisted sorting
- Melting, usually with the addition of melting salts and removal of oxidic aluminium component

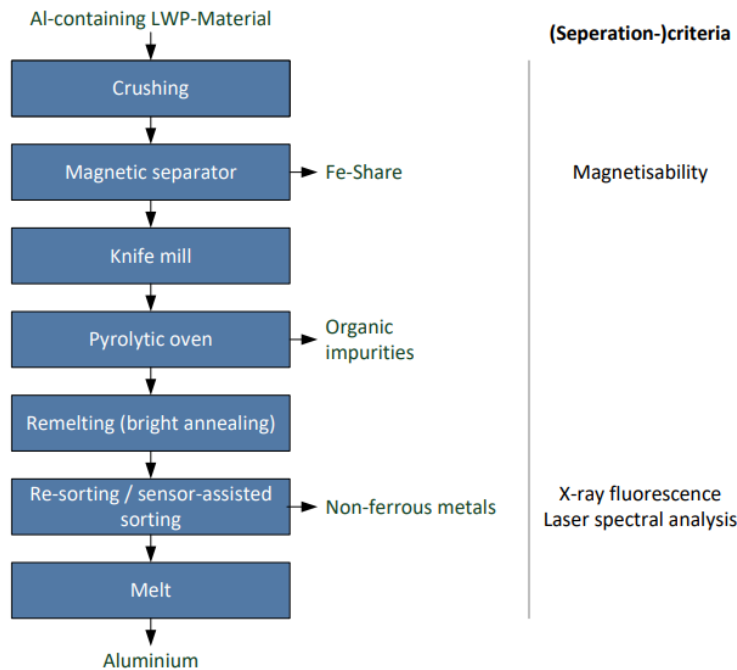


Figure 3-6: Recycling process of LWP aluminium.

3.7 Tinplate / ferrous metals

Tinplate or ferrous metal packaging, collected as part of the LWP collection or in the bring system, enters the packaging stream as food cans, for example. Due to its ferromagnetic properties, tinplate packaging is very easy to separate from the rest of the LWP mixture.

The steps carried out for processing are (see Figure 3-7):

- Crushing for the decomposition of the material
- Removal of metallic and organic impurities, using non-ferrous precipitators and separators, for example
- Melting through use in the electric arc furnace or in the oxygen converter when used in the blast furnace route. Organic impurities are oxidised by the injection of oxygen. Other inorganic elements either pass into the metal as alloy components⁴ or are separated as slag [UBA, 2016-1].

⁴ To separate the tin from the sheet steel in the case of tinplate, the waste is first subjected to electrolysis.

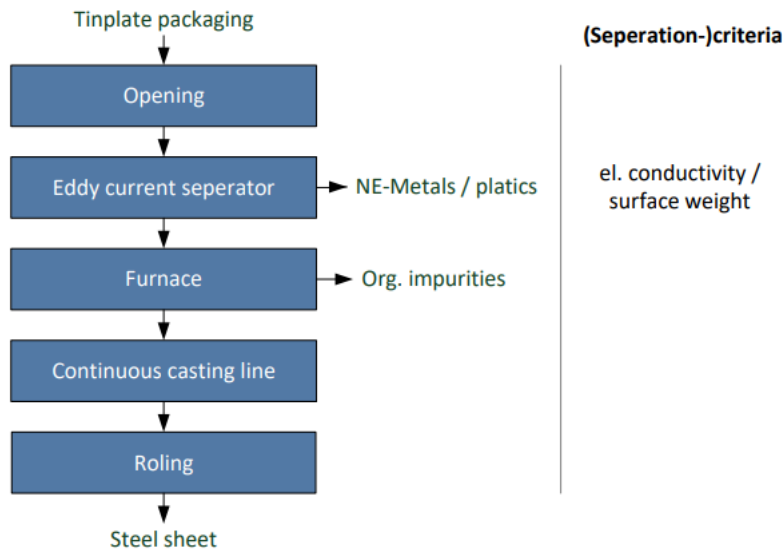


Figure 3-7: Recycling process of LVP tinplate

Cleaning is oxidised by the injection of oxygen. Other inorganic elements are either transferred to the metal as alloy components or are separated as slag [UBA, 2016-1].

3.8 PBC (Fibre-based packaging)

There is a material-specific recycling route for PBC packaging collected separately from other packaging waste in the collection or delivery system. The main raw materials for the recycling of PBC are graphic papers, corrugated cardboard, cardboard and other packaging papers. The proportion of value from the point of view of recycling is the fibre content. The process steps used for recycling serve the goal of separating the waste paper or the fibres from impurities and impurities and then making the fibres available for paper production. The essential steps in dry sorting of mixed PBC are according to the state of the art (see also Figure 3-8):

- Classification and/or removal of coarse and fine material with the use of ballistic separators
- Magnetic separation in order to separate ferrous metals
- Mechanical cardboard separation, with the use of a rotor sieve, for example
- Sorting of the material stream using near-infrared scanning systems (NIR)
- Manual final sorting by hand

The further preparation takes place in the paper mill, with the following steps:

- The waste paper material is suspended in a pulper with water (activation/pulping).
- The suspended fibrous material is then subjected to cleaning, among others, with the use of classifying units and vortex centrifuges (cleaning).
- Pigments, solvents and binding agents in the printing inks are dissolved and removed from the fibres. In the case of flotation deinking, water, caustic soda and soap are added to the

paper pulp in a flotation cell. Air nozzles create a foam to whose bubbles the ink components attach themselves. These float to the surface and are removed (ink removal / deinking).

The rejects that are removed during the preparation (contaminants, non-soluble components) are used for energy recovery.

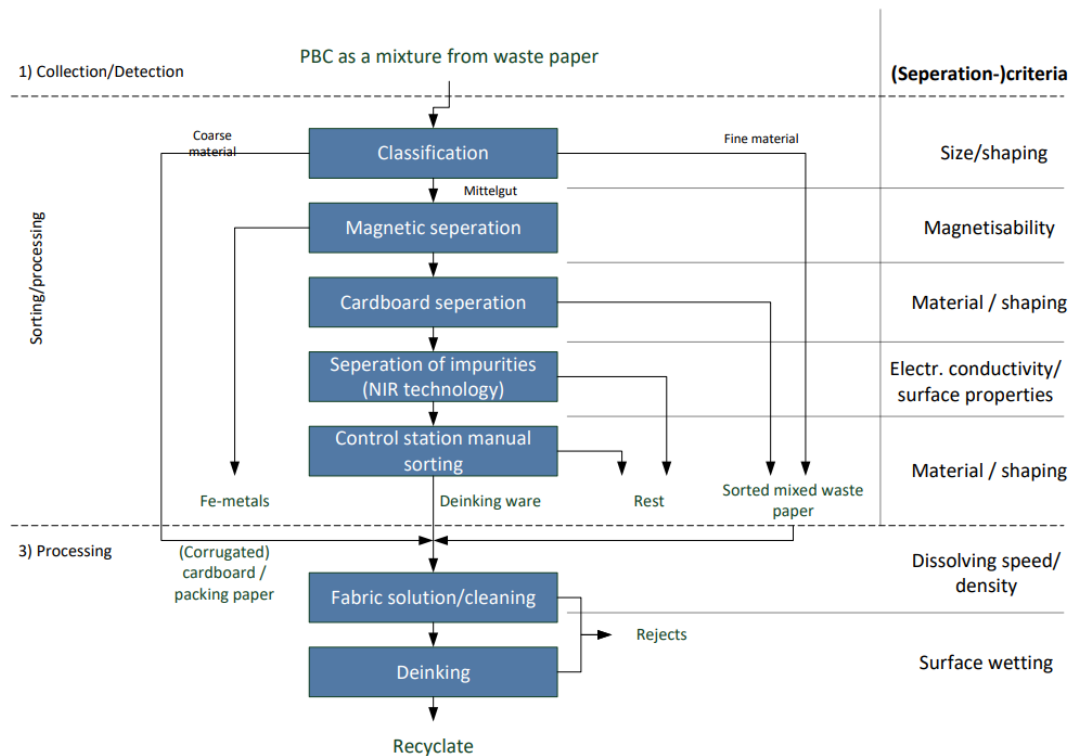


Figure 3-8: Process Steps PBC Recycling [UBA, 2016-1].

One of the challenges during the recycling process is printing inks which cannot be removed from the waste paper with the use of standard deinking processes. Problems are also caused by particular adhesive impurities, known as stickies (from adhesive labels or hot-melt adhesives in brochures, for example), which are fragmented and can therefore no longer be removed. Stickies can cause damage in the subsequent process. They can adhere to machine components which come into contact with the paper web and lead to web breaks [Gruber, 2011].

3.9 Container glass

- There is a material-specific recycling route for container glass collected separately by colour in the collection system. The purity of the used glass is the central requirement of the process. The main processing steps are (see [bvse 2016, [Erdmann et al. 2009] and [UBA 2024]):
- Coarse and colour sorting
- Shredding (e.g. roller crusher) and classification to ensure an optimised and homogeneous waste stream for the downstream sorting units
- Classification
- Separation of ferrous (magnetic separator) and non-ferrous metals (eddy current separator)
- Separation of adhering labels and contaminants, such as coatings or dust, either by mechanical label remover with drum dryer or extraction without further drying.
- Classification
- Light, flat contaminants (e.g. plastics) are separated using air separators
- Ceramics, stones and porcelain (CSP) as well as off-colours are selected using optoelectronic systems

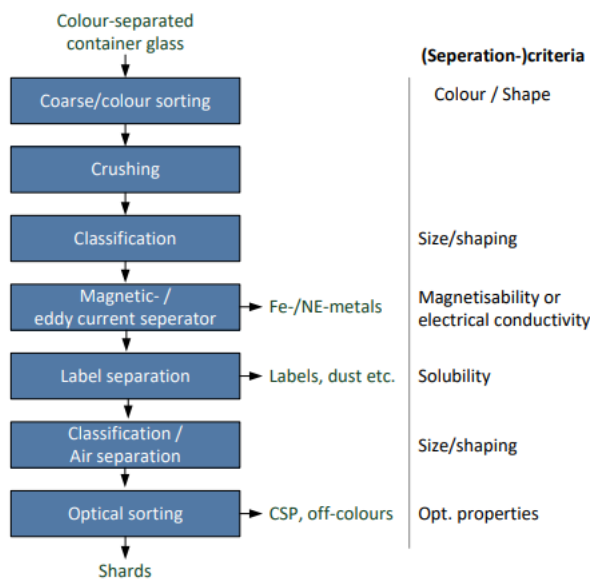


Figure 3-9: Process steps for container glass recycling

At the end of the process, a glass granulate is available that corresponds in quality to the original raw materials for container glass production. In the subsequent recycling in the glassworks, the processed waste glass is mixed with sand, soda, lime and aggregates, heated and melted.

4 Overview of assessment catalogue

The following describes a widely-applicable standard procedure for assessing the recyclability of packaging⁵.

The assessment system is divided into three levels, each of which is structured by specific assessment criteria:

- Assessment level 1: Allocation of packaging to the collection system
- Assessment level 2: Sorting capacity of mixed packaging (LWP)
- Assessment level 3: Suitability for mechanical recycling and provision of secondary products

In level 1, the ability to allocate the packaging to the intended collection system is highlighted. Level 2 essentially assesses the recyclability in terms of the target material as to whether, following collection in the form of a mix with other packaging, the packaging which is to be assessed can be identified or sorted for preparation for mechanical recycling processes. The key identifying attributes of mixed packaging are the magnetising capacity (tinplate packaging), electrical conductivity (aluminium packaging) and NIR identifiability of the surface (plastics, PBC, liquid packaging board).

Assuming that the packaging has generally been sorted into the sorting fraction⁶ intended for the target material, in level 3, the yield and quality of the secondary material obtained from the packaging are finally assessed. In this respect, the key criteria are the share of removable and non-recyclable packaging shares and unwanted inputs into the secondary product and/or the recycling process.

Prerequisites and assumptions for the evaluation of packaging are that

- the packaging is eligible for licensing
- the consumer correctly allocates the packaging or packaging components to the intended collection system for packaging - subject to the criterion described in Section 5.1 - without exception
- the consumer returns the entire packaging after use, i.e. without removing individual packaging components, to the designated collection system. Exceptions to this are packaging components
 - which must be intrinsically and irreversibly separated in order to use the contents (e.g. transparent film around CD cases, disposable tear-off caps, crown corks) or
 - which are loosely attached to the packaging material and must therefore be completely separated from the packaging material for normal use without separation measures by the consumer (e.g. cutting, twisting, tearing) (e.g. outer packaging, shelves, boxes for sweets, snap-on and snap-off lids),

which separate from each other solely as a result of mechanical stress during transport or preparation for sorting; the recyclability of these packaging components must be assessed separately from the actual packaging material.

⁵ Definitions of the term “packaging” according to the Packaging Ordinance (VerpackV) Annex V (to Section 3 (1) no. 1).

⁶ Regarding the management of special cases for consideration in level 3, see Figure 7-1

Not taken into account are the possible separation by the consumer of packaging combinations which can be pulled apart by hand and their material-specific delivery to the corresponding collection systems (in this context, a “3K yogurt pot” would be assessed as a packaging unit consisting of a plastic cup, a paper sleeve and a plastic/aluminium lid).

- the packaging is allocated a target material in the recycling process.
As the further sorting (level 2) and preparation (level 3) of packaging is basically material-specific, for the further recycling process, the type of determining packaging material must be defined in terms of the understanding of the accepted material or the target material. According to [ZSVR 2024], in the case of tinplate or aluminium packaging or composite packaging containing metal (such as multilayer packaging with aluminium layers, aerosol cans, composite cans with tinplate bottoms, but not metallised packaging and cups with aluminium plates and LPB), the respective metal is always the target material for recycling. Otherwise, the target material is generally considered to be the packaging material with the largest weight share of the packaging. If, in exceptional cases, a material which is only used as a packaging aid, for closures or wrappings, for example, has the largest weight share, the target material is determined differently in accordance with the packaging material on which the packaging is based⁷ (for example, a cup, bag, can, bottle, tray or tube).

Due to the considerable variety and development dynamics in the design of packaging, it may be possible in individual cases that a recyclability assessment is appropriate which, due to particular information situations or circumstances⁸, diverges from the standard procedure. Divergences from the standard procedure are then to be shown and justified accordingly.

The following table summarises the criteria for assessing the recyclability and their relevance to the possible target materials.

⁷ Packaging component which forms the main part of the packaging and is designed to hold packaged goods. It is used for the partial or complete wrapping, and in its final state, forms an open or closed hollow container. (see DIN 55405).

⁸ During the assessment of packaging made of wood or ceramics, for example.

Table 4-1: Overview of criteria catalogue. X = criterion to be applied to corresponding target material.

Criterion	Abbreviation										
		PE	PS	PP	PET	LPB, PBC comp.	Tinplate / Fe	Aluminium	PBC	Glass	
Level 1 Allocation of the packaging to the collection system											
Can the intended collection system of the packaging be allocated by the consumer?	Collection system can be allocated	X	X	X	X	X	X	X	X	X	X
Level 2: Sorting capacity of mixed packaging collected											
Is the packaging large enough?	Minimum size	X	X	X	X	X		X			
Identifiability of tinplate packaging: Is the packaging magnetisable? (magnetising capacity) ¹⁾	Magnetising capacity	X	X	X	X	X	X				
Identifiability of Al packaging: Is the packaging sufficiently electrically conductive? (Conductivity) ¹⁾	Conductivity	X	X	X	X	X		X			
Identifiability of packaging made of plastic, LPB, PBC composite, PBC and glass: Is the packaging recognisable from its surface?	Surface characteristics	X	X	X	X	X			X ²	X ²	
Level 3 Suitability for mechanical recycling and provision of secondary products											
Can a high-quality form of recycling be expected for the packaging?	Extent to which the recycling method is high-quality	X	X	X	X	X	X	X	X	X	X
Does the packaging contain non-recyclable shares that can be separated during processing?	Separable, non-recyclable shares	X	X	X	X	X	X	X	X	X	X
Does the packaging introduce (non-removable) impurities with the risk of contaminating the recycled product and/or disrupting the recycling process?	Non-separable shares and/or impurities	X	X	X	X	X	X	X	X	X	X

¹⁾ Target material plastic and/or PBC composite (not LPB): test for identification on basis of TP and/or small Al shares

²⁾ Packaging made of glass and PBC are collected separately from the LWP mixture as mono-material. The identification of PBC (via NIR) and glass (via visual sorting) as target materials does not therefore take place within the scope of LWP sorting, but downstream in the actual mechanical recycling process. Notwithstanding this, the assessment of identifiability is formally allocated to level 2 for reasons of clarity. As a rule (for exceptions, see [ZSVR 2022] or Table 6-7), the identifiability or sorting capacity of packaging made of glass and PBC can be assumed to be given.

5 Level 1: Allocation of the packaging to the collection system

5.1 Can the intended collection system of the packaging be allocated by the consumer? (Collection system can be allocated)

Explanation

To ensure the recyclability during the sorting and preparation, the consumer is required to take the packaging to the designated collection system after use. In general, it is therefore necessary for the consumer to decide whether the packaging is intended for LWP, PBC or container glass collection⁹. Under certain circumstances, packaging in which LWP materials (for example, plastics and aluminium) are combined with PBC can therefore lead to challenges with the allocation¹⁰. This can be particularly the case with packaging designs in the form of compounds or in the case of specific packaging aids (for example, cardboard label sleeves for yogurt pots). Disposal instructions provide the possibility for supporting the consumer with their decision in the case of packaging designs that may potentially be difficult to allocate.

Operational implementation assessment

Table 5-1: Assessment of the “can be allocated to collection system” criterion

Aspect	Explanation
Technical information requirement for the assessment	Packaging materials, weight shares, target material (for definition, see section 4)
Assessment method, tool	Determination on the basis of the packaging sample provided. If the target material is not clearly identifiable, completion of appropriate laboratory analyses on the types of material used and their weight shares

⁹ The separate collection of metallic packaging is also possible in some cities or districts

¹⁰ In the case of combinations of LWP material (in most cases, closures) with container glass or possibly Fe metal, for the purposes of simplification, no difficulties are assumed for the allocation to the material-specific collection system.

Table 5-2: Assessment of the “can be allocated to collection system” criterion

Classification / assessment	Explanation Classification
Intended collection system for consumers can be allocated intuitively <u>without any problems</u>	Packaging only consists of the LWP materials plastic, aluminium, tinplate or paper and/or container glass. Paper packaging aids (labels) only account for a small weight share (significantly less than 20% by mass)
Intended collection system for consumers can be allocated intuitively to a <u>limited extent</u>	Packaging material is LPB or Packaging material is a PBC-based composite and/or Packaging material is plastic, and packaging aids made of PBC have a considerable weight share (significantly more than 20 mass %). The packaging contains printed information regarding the intended collection (in this case, simply printing a recycling symbol equivalent to the “Green Dot” is not sufficient).
The intended collection system is <u>difficult</u> for consumers to allocate intuitively	Packaging material is a PBC-based composite and/or Packaging material is plastic, and packaging aids made of PBC account for a considerable weight share of the packaging. The packaging does not contain printed instructions on its intended collection.
The intended collection system <u>cannot</u> be allocated on the part of the consumer	Packaging material is neither plastic, LPB, PBC composite, aluminium, tinplate nor paper and/or container glass

6 Level 2: Sorting capacity of mixed packaging (LWP) collected

6.1 Is the packaging large enough? (Minimum size)

Explanation

The minimum size of a piece of packaging is a key characteristic in terms of the successful sorting of mixed LWP. If the packaging falls below a minimum size, it is highly likely that it will be rejected in the first stages of the sorting, i.e. it will not be sorted to the required depth for high-quality recycling. An exception is ferrous metal packaging and/or packaging components (such as crown caps), which are usually removed from small material streams with a high degree of sorting success:

- The classification of the primary material into two to three size categories takes place using drum sieves¹¹. Narrowing down the grain spectrum to a specific minimum and/or maximum is necessary to ensure that the subsequent sorting units are able to work efficiently. Packaging which falls below the minimum size can only be allocated to the correct target fraction to a limited degree.
- The air nozzle bar of an NIR sorting unit has a distance between each discharge blower (air nozzle) (see Figure 6-1). The nozzle distances are usually in a range of 12.5–37.5 mm. Packaging which is smaller than the nozzle spacing is less likely to be discharged; packaging of a sufficient minimum size is highly likely to be discharged.

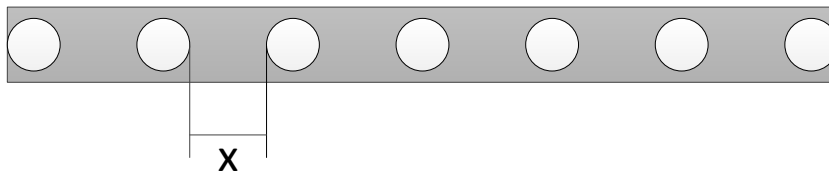


Figure 6-1: Schematic representation of an NIR air nozzle bar with a nozzle spacing of 12.5 – 37.5 mm

The lower grain size in the classification (drum sieving) is usually in the range of 20 to 50 mm. Therefore, 20 mm is set as the required minimum size for the packaging, as this also allows for a separation using an NIR sorting unit.

Operational Execution Evaluation

Table 6-1: Evaluation of the minimum height criterion

Aspect	Explanation
Need for technical information on the assessment	Size, dimensions of packaging.
Evaluation method, tool	Determination by means of apparent observation of the packaging sample, supplemented by a laboratory test if necessary (laboratory test: Measuring the packaging or the packaging must not pass through a round opening with a diameter of 20 mm)

¹¹ Either a large drum sieve with two screen cross-sections or two drum sieves, each with one screen cross-section are used.

Table 6-2: Evaluation of the minimum height criterion

Classification / assessment	Explanation classification
Packaging has a sufficient size	Packaging is larger than 20 mm in two dimensions
Packaging does <u>not</u> have sufficient size	Packaging is smaller than 20 mm in two dimensions

6.2 Identifiability of tinfoil packaging: Is the packaging magnetisable? (Magnetising capacity)

Explanation

Packaging that can be magnetised can be removed from the packaging stream with a high degree of separation efficiency and yield. In most cases, a magnetic separator is installed after the classification process above a conveyor belt or a discharge edge at a maximum distance of 1 m. To allow the packaging to be removed and enter the intended recycling path for iron packaging, it is necessary for it to have sufficient ferromagnetic properties.

Tinfoil (iron) is normally used for packaging, in the form of cans, for instance. Labels, coatings or protective layers made of plastics do not generally have a negative effect on the sorting with magnetic separators. It can be assumed that the iron share of the tinfoil packaging is usually sufficiently high and the magnetic separation is guaranteed.

Operational implementation assessment

Table 6-3: Assessment of the magnetising capacity criterion

Aspect	Explanation
Technical information requirement for the assessment	Magnetising capacity or Fe share
Assessment method, tool	<p>Magnetising capacity is a separation feature that enables a high degree of sorting success. If TP is the material with the largest weight share of the packaging, as a general rule it can be assumed that the packaging can be sorted and separated without restriction.</p> <p>For packaging with lower shares of TP (small shares, although TP is the target material), the identifiability must be estimated. If in doubt, carry out plant or laboratory tests.</p> <p>The following set-up is suggested for a laboratory experiment: A cuboid ferrite permanent magnet is to be used for the laboratory experiments. The dimensions of the magnet should total at least 10*10*5 cm. The magnet is placed at a distance of 5 cm ¹² above the packaging to be tested. The packaging must be tested in different positions underneath the magnet. If the packaging is lifted by the magnet in all positions, the packaging is to be assessed as magnetisable.</p>

¹² Distance for the described laboratory magnet (10*10*5 cm). For other laboratory magnets, the distance may have to be adjusted.

Table 6-4: Assessment of the magnetising capacity criterion

	Simplified assessment	Plant / Pilot plant trial
Classification / assessment	TP is the target material and material with the largest weight share in the packaging (e.g. can)	TP is the target material, although TP does not have the largest weight share in the packaging (composite containing metal)
Detection of TP possible without restriction.	No test required, as it is assumed that a detection is possible in all cases	Detection of TP takes place in all examined positions
Detection of TP limited or not possible	-	If the detection of TP only takes place in part of the possible positions to be examined, the <u>sorting behaviour of the packaging is assessed on the basis of the material with the largest weight share (for example, plastic or paper)</u>

6.3 Identifiability of Al packaging: Is the packaging sufficiently electrically conductive? (Conductivity)

Explanation

Based on the electrical conductivity of a piece of packaging, the specific production of a non-ferrous metal fraction is possible (especially aluminium). Eddy current separators are used to separate this fraction. For the precipitation, these make use of the formation of eddy currents in electrically-conductive materials in the presence of changing magnetic fields. In principle, it is irrelevant as to whether the conductive layer (for example, aluminium film) is enclosed by other layers (PBC, plastic). In general, success of the outcome increases with the surface area and the layer thickness of the non-ferrous metal as well as the share of the Al mass in terms of the overall packaging. It is also important to distinguish between whether the packaging contains aluminium film, or whether it has only been vapour-deposited with aluminium¹³.

Commonplace packaging containing aluminium includes yogurt pot lids, vacuum packaging for coffee, aluminium films, aluminium tubes, pet food trays, empty tablet packaging (aluminium-plastic blisters) or coffee capsules. Aluminium can be the original target material of the packaging or, in combination with the target materials of plastic and PBC¹⁴ in particular, it may have a small share. If Al is used as both a target material and a small share, its identifiability must be checked on the basis of the conductivity.

¹³ Vapour-deposited aluminium layers have a high pore content, so their conductivity is significantly limited.

¹⁴ But not LPB, which is produced upstream in the sorting chain as a separate fraction through NIR detection

Operational implementation assessment

Table 6-5: Assessment of the conductivity criterion

Aspect	Explanation
Technical information requirement for the assessment	Electrical conductivity or Al share
Assessment method, tool	<p>If Al is the material with the largest weight share of the packaging, it can be generally assumed that the packaging can be sorted using an eddy current separator.</p> <p>In the case of lower Al shares (small Al share, although Al is the target material), plant or pilot plant tests must be carried out in case of doubt. The eddy current separator must correspond to an eddy current separator used in an actual LWP plant operation in terms of the key setting parameters (see Figure 6.2). The packaging to be tested is to be tested in different positions on the eddy current separator. If the packaging progresses beyond the point of separation in all positions, the packaging is to be assessed as electrically conductive.</p>

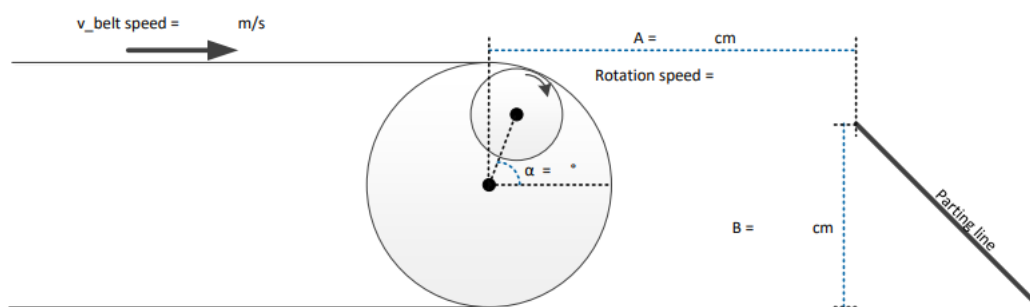


Figure 6-2: Sketch of an eddy current separator with eccentrically mounted pole wheel and the key adjustment parameters (belt speed, angle of the pole drum, rotational speed, distance and height of the point of separation)

Table 6-6: Evaluation of the criterion of electrical conductivity

	Simplified assessment	Plant/ pilot plant trial
Classification / assessment	Al is the target material and the material with the largest weight share in the packaging (e.g. can)	Al is the target material, although Al does not have the largest weight share in the packaging (e.g. composite containing metal)
Detection AI possible without restrictions.	No test required, as it is assumed that a detection is possible in all cases	Detection of AI takes place in all possible positions to be examined
Detection AI limited or not possible	-	If the detection of AI only takes place in part of the examined positions, the <u>sorting behaviour of the packaging is assessed on the basis of the material with the largest weight share (e.g. plastic or paper)</u>

6.4 Identifiability of packaging made of plastic, LPB, PBC composite and/or PBC and glass: Is the packaging recognisable from its surface? (Surface characteristics)

Explanation

The surface characteristics criterion is key to the identification of plastic packaging, liquid packaging board (LPB) and paper composites (PBC). Most sorting plants distinguish between different types of plastic (PET, PE, PP, PS, etc.) and their composites with the use of NIR (near infrared) measuring technology, and remove them from the waste stream with the use of compressed air. The conditions for a successful NIR sorting process depend on various factors:

- Detectability of the target material on the surface
 - Type of surface material
 - Structure and layer thicknesses of composite materials (multi-layer)
 - Surface colour
 - Reflection behaviour
- Several detectable materials have a share in the surface (for example, a bottle made of PE with a lid made of PP) and the position of the packaging on the sorting belt (in the case of flat packaging with a multi-layer structure in particular, different materials can be detected according to the side facing the separating unit)

The surface colour and its reflective behaviour are decisive factors that significantly influence the sorting capacity. Surfaces which are reflective or have a metallic coating reflect the near-infrared radiation non-specifically, so that a detection of the material is impossible. Dark or black materials absorb the near-infrared radiation. This serves to prevent a reflection towards the detector unit. The recognition of the material and the output as the target fraction is impossible. Plastics which are coated in this way or are dark-coloured cannot be transferred to the correct recycling path and end up in the sorting residues or mixed plastics fraction.

Packaging which consists of several materials also poses problems for the identification. In principle, a piece of packaging can be designed on a multilayer basis (different material layers)

and/or with several packaging components, such as packaging aids. The NIR detection of packaging with multilayers is influenced by the layer structure, the respective layer thicknesses, the materials used and individual settings of the NIR sorting system. A complete coating with impurities could also, in principle, lead to a correct identification of the target material if the layer thickness of the impurities is sufficiently low and the reflection behaviour is favourable.

Ultimately, however, the points at which the surface measurements are taken is decisive. The probability of a correct allocation to the target fraction increases with the surface share of the target material. If more than 30% of the surface of the target material consists of impurities¹⁵, there is a high probability that a correct identification of the target material cannot take place. Labels, printing or wrappings can therefore have a negative effect on the NIR detectability of the target material if they are not made of the target material. Closure systems (lids, caps, screw caps, sealing films, pourers, dispensers, etc.) made of impurities can also prevent the packaging from being allocated to the correct target fraction. In both of the aforementioned cases, there is a risk that the material of the packaging aid will be detected. This also depends on the position of the packaging on the sorting belt (especially in the case of flat packaging) and on the technical specifications of the NIR separator.

Large, flat, flexible plastics (films) occupy a special position.

Flat packaging makes the identification of other packaging difficult or impossible, especially when it covers it. Plastic films are also more difficult to remove using the NIR technique, as the flight behaviour during the blowing out process is diffuse. Flexible plastics can also change their position on the NIR detection belt at high belt speeds. The targeted blowing out is no longer possible. To prevent these effects, large-scale flexible plastics are separated out at the beginning of the sorting process using an air separator and are usually fed in as a separate fraction for further recycling after the manual product control.

For this type of packaging, the identification and/or sorting can also be carried out with the weight per unit area instead of the NIR detection of the surface. As part of this assessment methodology, an output is assumed from an area of > DIN A4, regardless of the plant-specific equipment settings.

Packaging made of glass and PBC is collected separately from the LWP mixture as mono-material. The identification of PBC (via NIR) and glass (via visual sorting) as target materials does not therefore take place within the scope of LWP sorting, but according to the material-specific, separate collection in the actual mechanical recycling process. Notwithstanding this, the assessment of identifiability is formally allocated to level 2 for reasons of clarity. As a rule (for exceptions, see [Table 6-7]), the identifiability and/or sorting capacity of packaging made of glass and PBC can be assumed to be given.

¹⁵ Plastics Recyclers Europe: www.plasticsrecyclers.eu

Operational Execution Evaluation

Table 6-7: Assessment of the surface characteristic criterion

Aspect	Explanation
Technical information requirement for the assessment	<ol style="list-style-type: none"> 1. Colour and reflectivity of the surface/s 2. For different surface materials: Distribution of the surface in percentage (also, position dependency) 3. Special case of flexible plastics: Surface area, dimensions of the packaging.

Assessment method, tool

According to [ZSVR 2024], empirical testing of identifiability/separability in trials is generally not required. **Packaging features that do, however, require an identifiability/separability test by means of trials are**

Plastic packaging

- Large-area labelling (> 50 % of the surface) with foreign material
- Full sleeve labelling (exception: full sleeves without light barrier of PET hollow bodies - clear or light blue - when using OPS, PET or PO sleeves)
- Multilayer structure (except: PE/PP-EVOH)
- Metallisation (except inside / metallised in the middle layer)
- Colouring using carbon black-based dyes (also when used in inner layers)
- > 50 % full-surface black printing (incl. background colour) using carbon black-based pigments
- Different types of plastic on the front and back sides
- Metal pigments applied over a large area (> 50% of the projected surface) (lacquering, coating or embossing)
- Nets

Fibre-based composite packaging / PBC composites

- Fully coated surface
 - except clear protective coatings up to a coating thickness ≤ 5 micro-metres or
 - except on the inside of pouches, bags and carrier bags, if the paper grammage is at least 100 g/m²
- Plastic-coated surface
 - except on the inside of bags, pouches and carrier bags, if the paper grammage is at least 100 g/m²
- Metal pigments (lacquering, printing, coating or embossing) applied over a large area (> 50 % of the projected surface)
- coloured black using carbon black-based pigments
- >50 % printed in black over the entire surface (incl. background colour) using carbon black-based pigments

Fiber-based packaging / PPK packaging

- Fully coated surface
 - (except clear protective coatings up to a coating thickness ≤ 5 micro-metres or
 - except on the inside of bags, pouches and carrier bags, if the paper grammage is at least 100 g/m²
- Plastic-coated surface
 - except on the inside of bags, pouches and carrier bags, if the paper grammage is at least 100 g/m²
- metal pigments (lacquering, printing, coating or embossing) applied over a large area (> 50 % of the projected surface)

LPB

- design deviating from the standard structure (non-wet-strength cardboard, PE \pm aluminium)

- Metal pigments applied over a large area (> 50 % of the projected surface) (painting, printing, coating or embossing)
- > 50 % full-surface black printing (incl. background colour) using carbon black-based pigments

Glass

- lack of transparency or translucency (detection with optical sorting units in the ultraviolet or visible light wave range (wavelength range 400 nm-780 nm))

The assessment is based on

- visual assessment of whether there are packaging features that require inspection (otherwise it is assumed that the product can be identified without restriction)
- in the special case of flexible plastics: determination by means of visual inspection or measurement of the packaging sample
- Test to assess the identifiability (if corresponding packaging features are present)

According to [ZSVR 2024], the test should be carried out using a standard detection unit. The following procedure is suggested for a test: In at least 10 runs, the packaging is fed to the NIR separation unit, e.g. by throwing it onto or dropping it onto the feed belt (the position of the packaging to be expected in reality should be taken into account via the random feed position) and the percentage allocation to the sorting fractions into which the packaging is discharged is determined over all runs.

Table 6-8: Assessment of the surface characteristic criterion

Classification / assessment	Simplified assessment	Test (required if the attribute according to [ZVSR 2024 Annex 2] is available)
Detection and separability of target material possible without restriction.	There is <u>no</u> packaging attribute according to [ZVSR 2024 Annex 2 or Table 6-7], or the packaging has a surface area clearly >DIN A4 (special case of flexible plastic)	A correct allocation of the target material takes place in at least 95% of all cycles.
Detection and separability of target material restricted		A correct allocation of the target material takes place in 75% to 95% of all cycles.
Detection and separability of target material clearly restricted		A correct allocation of the target material takes place in 75% to 50% of all cycles.
Detection and separability of target material impossible		A correct allocation of the target material takes place in less than 50% of all cycles.

7 Level 3: Suitability for mechanical recycling and provision of secondary products

The starting point for the assessment in level 3 is that the packaging is generally sorted into the fraction which is intended for the target material.

In special cases, in the case of LWP materials for which the sorting capacity of the target material is not given, the actual sorting fraction to be expected for the packaging or its recycling method is to be assessed in level 3 instead of the fraction which is intended for the target material. The corresponding decision-making grid is shown in the following figure.

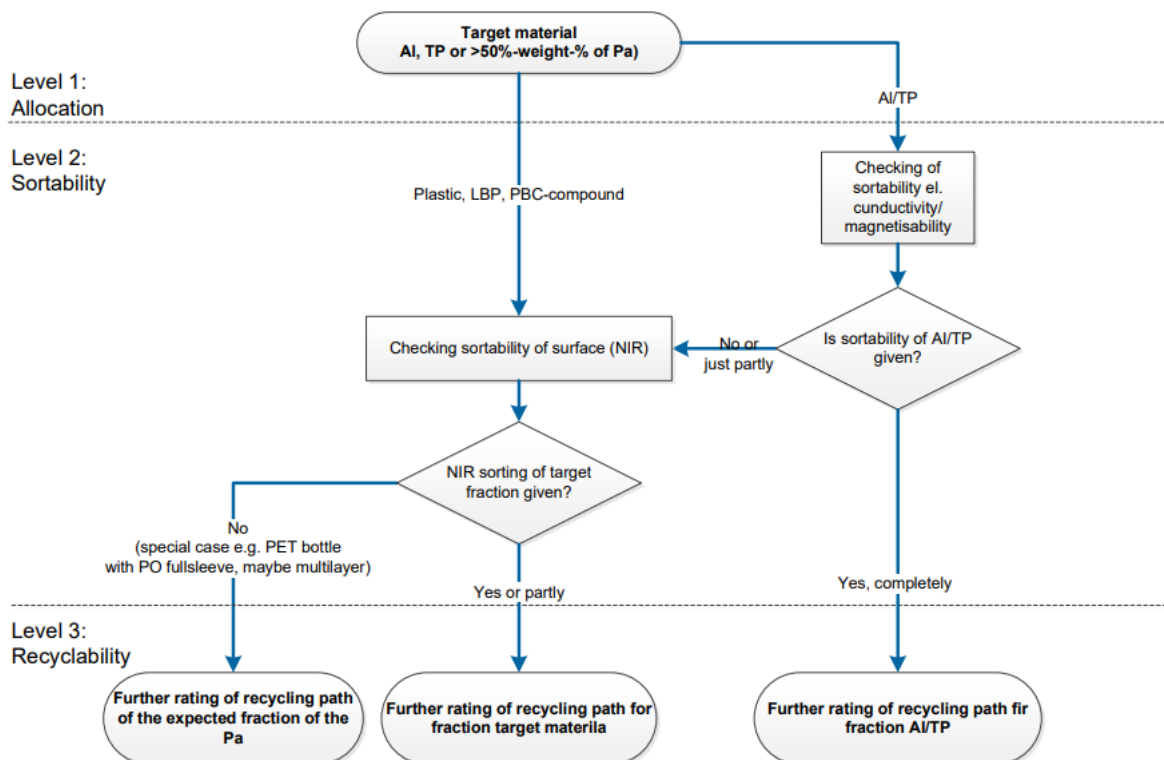


Figure 7-1: Selection of the recycling method for assessment in level 3 for mixed packaging (LWP).

7.1 Can a high-quality form of recycling be expected for the Packaging? (Quality of the recycling method)

The fractions to be yielded from the LWP sorting and pressed as baled goods, and the packaging collected separately on a material-specific basis from the PBC and container glass, are sent for recycling. The marketing depends strongly on the quality of the material and the current marketing prices. In the status quo, sorted plastics (PP, PE, PET, PS, films), metals, liquid packaging board, PBC and container glass, apart from non-material shares, are generally recycled mechanically and then returned as secondary products to the plastics processing industry or to aluminium, steel, glass and paper manufacturers.

The method presented here for assessing the recyclability prioritises high-quality mechanical preparation methods with a view to the potential reuse of the recycled products as a substitute

for the original primary material. In terms of this method, packaging used for the purposes of energy recovery is generally classified as being non-recyclable.

The recyclability assessment is carried out in relation to the material-specific collection and recycling processes that are relevant in Germany today. Today, high-quality mechanical recycling is generally only available for certain packaging materials. These packaging materials are iron, aluminium, container glass, PBC, LPB and the plastic types PE, PP, PS and PET (for example, transparent bottles). For other packaging materials (for example, PVC, biodegradable plastics or natural materials such as wood), no recyclability can currently be assumed¹⁶.

Today, there are very few buyers for the mechanical recycling of sorted mixed fractions made from transparent PET bottles and other PET packaging materials (for example, trays, blister packs), as different types of PET are used which cannot be recycled together or can only be recycled together mechanically on an extremely limited basis.

These difficulties mean that at present, only PET bottles are sent for high-quality mechanical recycling, while other PET fractions (for example, PET trays) are mostly used for energy recovery [Öko-Institut 2016].

The following table summarises the preparation methods which may be expected in the status quo and an assessment in terms of high-quality.

Table 7-1: Overview of recycling methods

Sorting fraction	Recyclable material	Expected type of recycling in terms of recyclable material [ZVSR 2024]	Decomposition [ZVSR 2024]
PE, rigid, semi-rigid	For blow-moulded or injection-moulded products: HDPE (PO)	High-quality mechanical	Cartridges for sealants
PP, rigid, semi-rigid	For injection moulded products or thermoforms: PP (PO)	High-quality mechanical	Cartridges for sealants
PS, rigid, semi-rigid	For injection moulded products: PS, dimensionally stable PE and PP content	Only high-quality mechanical to limited extent	foamed plastics incl. EPS products
PET bottles transparent, clear or coloured (PET-A)	For bottles (not contact-sensitive) or thermoforms or packaging tape: PET; PO from closures	High-quality mechanical	Opaque PET bottles and other PET products
Other PET packaging (PET-A) such as trays, lids, cups and other thermoforms	For thermoforms or packaging tape: PET	Predominantly energy recovery / only high-quality mechanical in individual cases	-
PE, large-format films ≥ DIN A4	For blown film and injection moulded products: LDPE (PO)	High-quality mechanical	Aluminium-vapourised plastics

¹⁶ The quantities of packaging waste from biobased polymers (for instance, PLA/starch blends) in the LWP stream, for example, are still too small to carry out a generally possible but nonetheless uneconomical fraction and/or type-specific form of mechanical recycling.

Sorting fraction	Recyclable material	Expected type of recycling in terms of recyclable material [ZVSR 2024]	Decomposition [ZVSR 2024]
PP, large-format films ≥DIN A4	For injection moulded products or thermoforms: PO	Only high-quality mechanical to limited extent	Aluminium-va-pourised plastics
PE, flexible < DIN A4	For blown film and injection moulded products: PO	Only high-quality mechanical to limited extent	
PP, flexible < DIN A4	For injection molded products or thermoforms: PO	Only high-quality mechanical to limited extent	
EPS	EPS	Predominantly energy recovery / only high-quality mechanical in individual cases	
LPB (cardboard composites made of cardboard/PE or cardboard/aluminium/PE)	Fibre content (for corrugated base paper) PO content (for injection-moulded products) and Al content	High-quality mechanical	Other items made of paper, cardboard, carton
Other fibre-based composite packaging (without metallic main component) (→ PBC from LWP) such as laminated folding boxes, composite cans, coated papers, paper cups coated on both sides, wrappers, etc.	For corrugated base paper: fibre content	Only high-quality mechanical to a limited extent ¹⁷	Liquid packaging board, wax, paraffin, bitumen and oiled paper
PBC packaging, without composites such as corrugated board, folding boxes, paper bags	Fibre content	High-quality mechanical ¹⁸	Liquid packaging board, wax, paraffin, bitumen and oiled paper
Tinplate and thin sheet metal packaging as well as composites containing tinplate such as tin cans, aerosol, varnish and paint cans, tinplate containers, composite cans with tinplate bottoms	Fe and Al content	High-quality mechanical	

¹⁷ For packaging filled with liquid or paste contents, individual evidence must be submitted in accordance with the detailed provision in 4.2. [ZSVR 2022]

¹⁸ For packaging filled with liquid or paste contents, individual evidence must be submitted in accordance with the detailed provision in 4.2. [ZSVR 2022]

Sorting fraction	Recyclable material	Expected type of recycling in terms of recyclable material [ZVSR 2024]	Decomposition [ZVSR 2024]
Aluminium packaging and aluminium-based composites (for example, aerosol cans, trays, tubes) or composite packaging containing aluminium film, blister packs for tablets, stand-up pouches, dry soup bags, tubes	Al and Fe content For Al composites, only Al share	High-quality mechanical	
Container glass and glass packaging	Glass content; Fe and Al content from lids and closures	High-quality mechanical	Lead glass, non-processed safety glass, glass ceramics, lighting products, TV glass, quartz glass and other glass containing lead

Operational implementation assessment

Table 7-2: Assessment of the extent to which the recycling method is high-quality criterion

Aspect	Explanation
Technical information requirement for the assessment	Expected recycling method for the packaging
Assessment method, tool	Determination of the expected sorting fraction (see Figure 7-1) and allocation of an expected preparation method (see Table 7-1).

Table 7-3: Assessment of the extent to which the recycling method is high-quality criterion

Classification / assessment	Explanation Classification
Expected preparation method for the target material ¹⁹ of the packaging is high-quality mechanical	Sorting fraction films, PP, PE, LPB, non-ferrous metals, PET (transparent bottles) tinplate, PBC or container glass
Expected preparation method for the target material of the packaging is predominantly high-quality mechanical	<ul style="list-style-type: none"> • Rigid, semi-rigid PS • Large-format PP films ≥DIN A4 • Flexible PE < DIN A4 • Flexible PP < DIN A4
Expected preparation method for the target material of the packaging is only partly high-quality mechanical	<ul style="list-style-type: none"> • PBC from LWP
Expected preparation method for the target material of the packaging is only high-quality mechanical in individual cases and/or the preparation method for the target material of the packaging is exclusively for energy recovery	<ul style="list-style-type: none"> • Other PET packaging (PET-A) (exception in individual cases upon provision of proof) • EPS (exception in individual cases upon provision of proof) • Target material is <u>not</u> TP / Fe, aluminium, container glass, beverage carton, PBC, PE, PP, PS or PET or • Sorting residues are to be assumed as the expected fraction after sorting • Packaging excluded from a sorting fraction (see column 4 Table 7-1)

If, in individual cases, the existence of the infrastructure necessary for high-quality mechanical recycling and its use can be documented, an exception may apply. For the respective individual case, the documentation must include: Proof that the result of the recycling process is high value in terms of the minimum standard and proof that the recycling method was provided to an appropriate extent, as supported with a weighing slip, [ZSVR 2024].

¹⁹ In special cases, in the case of LWP materials for which the sorting capacity of the target material is not given, the actual sorting fraction to be expected for the packaging or its recycling method is to be assessed in level 3 instead of the fraction which is intended for the target material.

7.2 Packaging plastics (PE, PP, PS, PET)

7.2.1 Does the packaging contain non-recyclable shares that can be removed during the preparation steps? (Separable packaging components)

Explanation

During the preparation of standard packaging plastics, there are individual packaging components that are foreign to the material and interfere in the preparation process or can have a negative impact on the quality of the recycled product. However, some of these non-recyclable packaging shares can usually be removed in the various steps of the preparation process (washing, float and sink separation, melt extrusion).

- The washing usually takes place in aqueous medium. The purpose of the washing is to clean product of adhesions and to remove or detach labels, foreign materials and other unwanted components such as prints.
- Subsequently, a density separation (float and sink separation) of the previously crushed and washed packaging is usually carried out so that the requisite plastic fraction can be enriched further. With the use of water, plastic types with a density greater or less than 1 g/cm³ are separated from each other. During the preparation of polyolefins (density < 1 g/cm³), plastics and other materials with a density > 1 g/cm³ can be removed as a sink fraction. Density separation reaches its limits for plastic types with small density differences. Plastics with a similar density such as PP and PE, for example, cannot be separated from each other. In this case, special liquids with a density which is between those of the target plastics can be used. However, this is rarely practised. During the recycling of PET (> 1 g/cm³), float and sink separation can be used to separate and recycle closures in particular, which are mostly made of PE-HD. The crushed components of the closure then end up in the light fraction and are therefore removed from the non-floating PET. PS (> 1 g/cm³) is also obtained as a sinking fraction and freed from specifically lighter PO shares. Changing the density of the original packaging material through the use of blends and additive compounds, for instance, can result in the introduction of impurities into the target fraction of the separation step or lead to the rejection of types of plastic from the target fraction that are actually wanted.
- During the further preparation of plastic fractions, the focus is on obtaining re-granulates (without additives) or regenerates (with additives) in the remelting process. During the extrusion / melting process, the shares that have a lower melting temperature compared with the processing temperature are also transferred into the re-granulate. These can cause a deterioration in the characteristics of the product (see Section 7.2.2). Therefore, the processing of composite materials, blends and plastics with additive compounds is potentially problematic. Although higher melting components can be separated and discharged as residues with the use of melt filtration, they increase the cleaning workload for the filter screen and also lead to yield losses of the target material during the course of the filtration. Low-melting components, on the other hand, find their way into the recyclate and/or decompose beforehand, which leads to a deterioration of the mechanical and visual characteristics of the recyclate.

The following is an overview of substances that can be removed during the course of the aforementioned preparation steps.

Table 7-4: Overview of removable, non-recyclable packaging components (according to the European PET Bottle Platform and Plastics Recyclers Europe). Processing temperatures for new goods according to Saechtling²⁰.

	Washing of the crushed packaging components	Density separation of the crushed, washed packaging components	Remelting process of the target fraction from the density separation
PE-HD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 160-220°C)
PE-LD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 180-250°C)
PP	Adhesives (water-soluble below 80°C, paper labels)	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 200-270°C)
PET, transparent bottles	Adhesives (water- or alkali-soluble in the temperature range 60 – 80°C), Paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 260-300°C)
PS	Adhesives (water soluble), paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS and with a density >1.08 g/cm ³ : PET, Al	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 170-280°C)

The PO shares of transparent PET bottles (especially caps) can be removed for further recycling during the course of the PET preparation (floating fraction of the density separation). Accordingly, further recycling can also be assumed for rigid PE and PP shares that are separated during PS recycling.

In the case of the other light or heavy fractions from the density separation of other types of plastics, energy recovery is usually the only solution because of the heterogeneous composition (various types of plastics or non-plastic materials).

²⁰ Processing temperatures for re-granulates tend to be lower

Operational implementation assessment

Table 7-5: Assessment of the removable packaging components criterion

Aspect	Explanation
Technical information requirement for the assessment	<p>Description of packaging materials and packaging aids (including adhesives), in particular with regard to</p> <ul style="list-style-type: none"> • Materials used (including composition and shares), shares of mass, structure • Solubility of the adhesives used • Density of the materials used, melting point and/or glass transition temperature <p>through examinations or on the basis of valid secondary information</p>
Assessment method, tool	<p>If no valid secondary information (for example, manufacturer's data or processing experience on incompatibilities of aggregates, for example, non-removable shares with the target material) is available on the packaging materials, studies on the solubility, density and remelting behaviour on a laboratory scale are helpful:</p> <p>Assessment of the solubility of adhesives / labels: The procedure taken could, for example, be equivalent to the Quick Test QT504 of the European PET Bottle Platform (www.epbp.org/page/8/downloads). The description of the experiment applies to PET. For the other plastic fractions, the procedure can be carried out in an aqueous phase in the respective temperature ranges indicated along the same lines as the procedure described in Quick Test QT504.</p> <p>Assessment of swim and sink behaviour: The procedure taken could, for example, be equivalent to the Quick Test QT502 of the European PET Bottle Platform. Alternatively, a density determination of packaging components after crushing (only non-foamed materials) can be carried out according to DIN 1183-1.</p>

Table 7-6: Evaluation of the criterion separable, non-recyclable packaging components²¹. Data in % by mass. Performance levels according to Annex II of the PPWR Amendments of the European Parliament to the Commission proposal of 18.04.2024. as additional information

Classification / assessment	Explanation classification	Performance levels and non-recyclable components according to PPWR draft Annex II ²²
Packaging does not contain <u>any</u> separable, non-recyclable shares	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging does not contain any non-material and removable shares (packaging made from mono-material)	Level A ($\leq 5\%$)
Packaging contains <u>small</u> shares	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging contains non-material and removable shares up to a maximum of 10%.	Level B ($>5\% - \leq 20\%$)
Packaging contains <u>relevant</u> shares	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging contains non-material and removable shares of between 10% and a maximum of 30%.	Level C ($>20\% - \leq 30\%$)
Packaging contains <u>significant</u> shares	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging contains non-material and removable shares of between 30% and a maximum of 50%.	
Packaging contains <u>large</u> shares	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging contains non-material and removable shares of more than 50%.	Technically not recyclable
Packaging is completely removed	The secondary information on the Packaging and/or the examinations carried out prove that the Packaging has been changed in terms of its characteristics (e.g. density), for example, by non-removable non-material shares (e.g. additive compounds or composites), in such a way that it is completely removed.	

7.2.2 Does the packaging introduce (non-separable) impurities with the risk of contaminating the recycled product and/or disrupting the recycling process? (Impurities with risks)

Explanation

In the understanding of this methodology, substances with a rather **low risk of contamination** are those substances in the packaging which, depending on their concentration, generally do not have a significant negative impact on the visual, mechanical or other characteristics of the

²¹ PO shares from PET recycling is not considered as separable but recyclable shares.

²² Amendments by the European Parliament to the Commission proposal of 18.04.2024 for a regulation of the European Parliament and of the Council on packaging and packaging waste, amending Regulation (EU) 2019/1020 and Directive (EU) 2019/904 and repealing Directive 94/62/EC of 18.04.2024. The exact calculation of the performance levels according to PPWR is laid down in delegated acts. The specification of the performance levels serves to orient the classification within the framework of this evaluation catalogue, which is carried out according to its own criteria.

recyclate and therefore its marketability. The recyclate only has minor restrictions in terms of processability and the downstream area of application.

Substances with a **significant risk of contamination** are substances in the packaging which, partially depending on the concentration, have such a significant negative impact on the visual and mechanical properties that the product expected from the preparation process may no longer be marketable and can only be used for the purpose of energy recovery. The recyclate then has considerable limitations in terms of its processability and area of downstream application.

The following table provides a simplified and non-exhaustive list of the typical impurities. The information is largely from the recommendations of [ZVSR 2024], Recyclclass²³ and [APR 2022]. The information in Table 7-7 provides an estimate of the process disturbances or impurities which are, in reality, to be expected for the materials mentioned. A specific assessment would generally require specific examinations. For some specific contaminations (according to [ZVSR 2024] and [APR 2021]), the recyclability of the packaging can generally be excluded.²⁴

Recycling incompatibility due to limited residual emptying of plastic packaging

Residual contents of special filling goods that remain in the packaging after use can increase the efforts for the recycling process of the packaging. For the contents silicones, acrylates, polyurethanes and other cross-linking substances, waxes and paraffins as well as bituminous compounds (selection according to [ZSVR 2024]), potentially limited emptying of residues of plastic packaging is therefore rated as contamination.

So far, relevant aspects that have to be taken into account for a specific evaluation of the emptying of packaging, such as "intended emptying" or a "minimum quantity threshold for product residues" have not yet been specified within the framework of the minimum standard. Until then, according to the minimum standard, the contents for plastic packaging silicones, acrylates, polyurethanes and other cross-linking substances, waxes and paraffins as well as bituminous masses are assessed as incompatibility with recycling.

For the time being, the assessment will be made in general and only based on the type of filling goods. Not considered are

- the characteristics of the contents (e.g. solid, liquid, viscous),
- amount of remaining content or
- Characteristics of the packaging design that hamper emptying

²³ <https://recyclclass.eu/recyclclass/design-for-recycling-guidelines>

²⁴ According to [ZSVR 2021], individual proof must be provided for a deviating determination of harmlessness regarding the recyclability of incompatible substances.

Table 7-7: Simplified overview of contamination with potential risk (according to [ZVSR 2024], <https://recyclclass.eu/recyclclass/design-for-recycling-guidelines>, [APR 2021], see also there for more detailed information on other packaging materials).

Target material	Low risk	High risk	Not recyclable [ZVSR 2024]
PE, flexible (for blown film and injection moulded products)	<p>Packaging material: Multilayer with ≤5% PP</p> <p>Barriers: ≤5% EVOH, metalised barrier layers</p> <p>≤1% PVOH (for coloured films according to Recyclclass)</p> <p>Packaging Ingredients: PP, PBC</p> <p>Colours / Prints:</p> <p>Prints <50% (transparent films)</p> <p>Prints >50% (colored foils)</p> <p>≤0.8% NC-based printing inks (according to Recyclclass for coloured films)</p>	<p>Packaging material: Multilayer PE/PP with >5% PP</p> <p>Barriers: >5% EVOH, PVOH (transparent films and >1% for coloured films according to Recyclclass)</p> <p>Packaging components: Metalised labels, all other materials with a density <1g/cm³</p> <p>Colours / Prints:</p> <p>Prints >50% (transparent foils), bleeding inks, toxic, dangerous inks</p> <p>>0.8% NC-based printing inks (according to Recyclclass for coloured films)</p>	<p>Fibre-containing labels if the cellulose content cannot be removed by means of cold washing</p> <p>PA layers, made of polyamide²⁵</p> <p>PE-X-components²⁶</p> <p>PVDC layers</p> <p>other non-PE polymeric layers (excluding adhesion promoters, adhesives, PP, EVA and EVOH)</p> <p>Non-polymer layers (except SiOx/AlOx/metallization)</p> <p>NC inks used in adhesive side printing.</p> <p>[APR 2024]: PVC</p>

²⁵ Individual evidence of polyamide-6 or co-polyamide 6/6.6 in co-extruded PE/PA(EVOH) films in combination with a MAH-grafted PE as an adhesion promoter (AP) in a ratio of at least 0.5 g AP per g PA (+EVOH) or polyamide-6 in laminated PE/PA films in combination with a MAH-grafted PE as a compatibility promoter (CP) in a ratio of at least 0.15 g CP per g PA

²⁶ Reference for PE-Xc < 50 kGy

Target material	Low risk	High risk	Not recyclable [ZVSR 2024]
PP flexible (for injection moulded products or thermoforms)	<p>Packaging material: Multi-layer with PE ($\leq 10\%$ according to Recyclclass),</p> <p>Barriers: EVOH ($\leq 5\%$ according to Recyclclass), metallised barrier layers</p> <p>Packaging Components: PE-, PBC</p> <p>Colours / Prints: Prints $< 50\%$ (transparent films) Prints $> 50\%$ (coloured films) Additive: PBT Voiding Agent $< 5\%$ (according to Recyclclass for coloured films)</p>	<p>Packaging components: Metallised labels, all other materials with a density $< 1\text{g/cm}^3$</p> <p>Adhesives: non-soluble</p> <p>Colours / Prints: Prints $> 50\%$ (transparent films), bleeding colours, toxic, hazardous inks</p>	<p>The silicone components; foamed non-thermoplastic elastomers with a density $< 1\text{g/cm}^3$; foamed non-polyolefinic components; Labels containing fibres if the cellulose content cannot be removed under the conditions of cold washing.</p>
HDPE rigid (for blow moulded or injection moulded products)	<p>Barriers: EVOH $< 1\%$²⁷</p> <p>Packaging components: (e.g. caps, labels, closures): PP $> 8\%$²⁸);</p> <p>Colours/prints: direct printing (coloured containers)</p>	<p>Packaging material: Multilayer HDPE + (PLA, PVC, PS, PET, PETG)</p> <p>Barriers: EVOH $> 1\%$; Aluminium</p> <p>Packaging components: metallisation or Al, PVC; foiled paper</p> <p>Inks/prints: bleeding colours, toxic, hazardous inks, direct printing (colourless containers),</p>	<p>The silicone component Fibrous labels if the cellulose content cannot be removed under the conditions of cold washing PET-Sleeves Dichte $< 1\text{g/cm}^3$ PA Barriers PE-X-Component PVDC barriers Non-PO plastics with a density $< 1\text{g/cm}^3$</p>

²⁷ Exception EVOH $> 6.0\%$ in combination with PE-g-MAH tie layers (MAH $> 0.1\%$) and EVOH to tie layers ratio ≤ 2 (<https://recyclclass.eu/de/novel-findings-for-functional-barriers-in-hdpe-containers/>)

²⁸ Assumption based on ISD information.

Target material	Low risk	High risk	Not recyclable [ZVSR 2024]
PP rigid (for injection moulded products or thermoforms)	<p>Barriers: EVOH<1%²⁹</p> <p>Packaging components: (e.g. caps, labels, closures): PE >8%³⁰)</p> <p>Colours/prints: direct printing (coloured containers)</p>	<p>Packaging material: Multilayer PP + (PLA, PVC, PS, PET, PETG)</p> <p>Barriers: EVOH >1%; Aluminium</p> <p>Packaging components: Metallisation, Al, PVC,</p> <p>Adhesives: non-soluble</p> <p>Inks/prints: bleeding colours, toxic, hazardous inks, direct printing (colourless containers),</p>	<p>Silicone components</p> <p>Components of foamed non-thermoplastic elastomers</p> <p>Fibrous labels if the cellulose content cannot be removed under the conditions of cold washing</p> <p>PET-Sleeves with a density <1g/cm³</p> <p>PA barriers</p> <p>PVDC barriers</p> <p>Non-PO plastics with a density < 1 g/cm³</p>
PS rigid (for injection moulded products)	<p>Barriers: EVOH</p> <p>Colours/Prints: Prints <50%</p>	<p>Barriers: PA, PVDC</p> <p>Colours/Prints: Prints >50%</p>	<p>Foreign plastics or multilayers of density class density 1.0 – 1.08 g/cm³</p> <p>Fibrous labels if the cellulose content cannot be removed under the conditions of cold washing</p>
PET Bottles Transparent (for bottles - not contact-sensitive, thermoforms or packaging tape) and other transparent, rigid PET packaging (thermoforms or packaging tape)	<p>Additives, filler materials: AA/UV blockers, O2 absorbers, brighteners</p> <p>Labels: lightly metallised labels, hot-melts</p> <p>Colours / Prints: Direct printing with production code, best-before date</p>	<p>Colours: transparent colours except "light-blue", opaque, fluorescent, metallic bottle colour</p> <p>Additives, filler materials: bio- / oxo- / photodegradable additives, nanocomposites</p> <p>Labels: heavily metallised labels, pulpable paper labels</p> <p>Adhesives: non-soluble</p> <p>Inks/Prints: Printing with bleeding inks, toxic, hazardous inks, direct printing; PE with water-soluble colour</p>	<p>PET-G-components, POM-components, PVC components</p> <p>EVOH layers, silicone components, PA monolayer layers for transparent PET bottles, colourless and "light-blue"</p> <p>PVC labels/sleeves, PS labels/sleeves, PET-G labels/sleeves, other labels/sleeves/printed top films with density (incl. printing and varnishing) > 1g/cm³</p> <p>Other blended-barriers</p> <p>PA additives for transparent PET bottles, colourless and "light-blue"</p> <p>Non-removable (washable) adhesive applications (in water or alkaline at 80°C)</p> <p>non-magnetic metals</p> <p>Elastomer components with a density > 1 g/cm³</p> <p>Direct printing (apart from production code, best-before date and UFI code61)</p> <p>[APR 2024]: Packaging components (labels, dosing products, etc..) with PVC PLA</p>

²⁹ Exception analogous to HDPE dimensionally stable

³⁰ Assumption based on ISD information.

Operational implementation assessment

Table 7-8: Assessment of the impurities with risks criterion.

Aspect	Explanation
Technical information requirement for the assessment	<p>Potential contaminations (for details, see https://recyclclass.eu/recyclclass/design-for-recycling-guidelines, [ZSVR 2024] [APR 2021]) shown in simplified form Table 7-7 in the packaging. In the case of doubt, further examinations and research on possible product / process risks of non-removable material combinations, adhesives, additive compounds, etc.</p> <p>Assessment of the potential capacity of the packaging to be completely emptied, or examinations by the distributors according to the Recyclclass method (easy-to-empty index)</p> <p>Type of content: Silicones, acrylates, polyurethanes and other cross-linking substances, waxes and paraffins as well as bituminous compounds</p>
Assessment method, tool	Laboratory testing with appropriate analytics (for example, DSC, micro-tome sections, filler material analysis: TGA (thermal gravimetric analysis) or solvent-based polymer digestion (IVV method).

Table 7-9: Assessment of the impurities with risks criterion.

Classification / assessment	Explanation Classification
Packaging does not introduce any unwanted impurities into the product or recycling process	No unwanted impurity that cannot be removed
Packaging introduces unwanted impurities with a low risk of contamination for the recycling product and/or process	The Packaging contains components with a low risk of contamination that cannot be removed in the preparation process (differentiated assessment according to the number of types of impurities).
Packaging introduces unwanted impurities with a high risk of contamination for the recycling product and/or process	The Packaging contains components with a high risk of contamination that cannot be removed in the preceding preparation process (differentiated assessment according to the number of types of impurities).
Packaging has unwanted impurities that preclude a recyclability	The Packaging contains components for which the recyclability of the packaging can be ruled out across the board, regardless of whether these can be removed in the preceding preparation process.

7.3 Fibre-based packaging (PBC packaging, PBC composite) and LPB

7.3.1 Does the packaging contain non-recyclable shares that are separated during the processing steps? (separable packaging components)

Explanation

The objective of recycling PBC packaging is to recover the fibrous material share from the packaging through repulpability. The fibre's ability to be defibrillated is crucial to the success of recycling. PBC packaging is treated in a pulper to break down the fibres. During this process, not only are remnants of the filling material removed, but also product adhesions and any

adhesive labels. Unwanted shares which can be removed during the preparation steps are recyclable adhesives and printing inks, wet-strength papers, non-material closure systems or staples, as well as EPS or plastic films and fibre components which cannot be broken down during the pulping process. When the fibre slurry is pressed through the screening system, all the substances that have not dissolved in the previous pulping step are usually removed and do not therefore have a negative effect on the material. This is always associated with a loss of fibre material, however. Additionally, non-paper substances can pass into the aqueous phase.

Compared with the recycling of PBC packaging, the pulping of LPB and other paper composite materials requires a special process with higher pulping times and a greater use of energy as well as a more complex reject line.

Non-recyclable, removable fractions are known as unwanted materials in recycled paper. They are classified as

- Non-paper components such as metals, plastics, synthetic materials, etc., and
- Non-paper substances which pass into the aqueous phase (water-soluble, colloiddally dissolved or finely dispersed) and
- Paper, cardboard and cardboard packaging which is unsuitable as a raw material for normal production (for example, composites of paper with plastic and/or aluminium, wet-strength papers, papers containing wax, lacquered papers).

Operational Execution Evaluation

Table 7-10: Evaluation of the separable packaging component criterion

Aspect	Explanation
Need for technical information on the assessment	Description of packaging materials and all packaging aids (including adhesives), in particular with regard to <ul style="list-style-type: none"> • Materials used (incl. composition and proportions), mass proportions, structure • Proportion of undesirable materials
Evaluation method, tool	Determination of the non-paper product components (incl. substances that pass into the aqueous phase) and the repulpability according to PTS method PTS-RH 025/2022 or CEPI Recyclability Laboratory Test Method (CEPI) / 4evergreen). The special process conditions in the recycling of paper composites and LPB, which are necessary to recover the fibre content, must be taken into account.

Valuation analogous Explanation

During the preparation of standard packaging plastics, there are individual packaging components that are foreign to the material and interfere in the preparation process or can have a negative impact on the quality of the recycled product. However, some of these non-recyclable packaging shares can usually be removed in the various steps of the preparation process (washing, float and sink separation, melt extrusion).

- The washing usually takes place in aqueous medium. The purpose of the washing is to clean product of adhesions and to remove or detach labels, foreign materials and other unwanted components such as prints.
- Subsequently, a density separation (float and sink separation) of the previously crushed and washed packaging is usually carried out so that the requisite plastic fraction can be

enriched further. With the use of water, plastic types with a density greater or less than 1 g/cm³ are separated from each other. During the preparation of polyolefins (density < 1 g/cm³), plastics and other materials with a density > 1 g/cm³ can be removed as a sink fraction. Density separation reaches its limits for plastic types with small density differences. Plastics with a similar density such as PP and PE, for example, cannot be separated from each other. In this case, special liquids with a density which is between those of the target plastics can be used. However, this is rarely practised. During the recycling of PET (> 1 g/cm³), float and sink separation can be used to separate and recycle closures in particular, which are mostly made of PE-HD. The crushed components of the closure then end up in the light fraction and are therefore removed from the non-floating PET. PS (> 1 g/cm³) is also obtained as a sinking fraction and freed from specifically lighter PO shares. Changing the density of the original packaging material through the use of blends and additive compounds, for instance, can result in the introduction of impurities into the target fraction of the separation step or lead to the rejection of types of plastic from the target fraction that are actually wanted.

- During the further preparation of plastic fractions, the focus is on obtaining re-granulates (without additives) or regenerates (with additives) in the remelting process. During the extrusion / melting process, the shares that have a lower melting temperature compared with the processing temperature are also transferred into the re-granulate. These can cause a deterioration in the characteristics of the product (see Section 7.2.2). Therefore, the processing of composite materials, blends and plastics with additive compounds is potentially problematic. Although higher melting components can be separated and discharged as residues with the use of melt filtration, they increase the cleaning workload for the filter screen and also lead to yield losses of the target material during the course of the filtration. Low-melting components, on the other hand, find their way into the recyclate and/or decompose beforehand, which leads to a deterioration of the mechanical and visual characteristics of the recyclate.

The following is an overview of substances that can be removed during the course of the aforementioned preparation steps.

Table 7-4: *Overview of removable, non-recyclable packaging components (according to the European PET Bottle Platform and Plastics Recyclers Europe). Processing temperatures for new goods according to Saechtling.*

Washing of the crushed packaging components	Density separation of the crushed, washed packaging components	Remelting process of the target fraction from the density separation
--	---	---

PE-HD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 160-220°C)
PE-LD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 180-250°C)
PP	Adhesives (water-soluble below 80°C, paper labels)	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 200-270°C)
PET, transparent bottles	Adhesives (water- or alkali-soluble in the temperature range 60 – 80°C), Paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 260-300°C)
PS	Adhesives (water soluble), paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS and with a density >1.08 g/cm ³ : PET, Al	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 170-280°C)

The PO shares of transparent PET bottles (especially caps) can be removed for further recycling during the course of the PET preparation (floating fraction of the density separation). Accordingly, further recycling can also be assumed for rigid PE and PP shares that are separated during PS recycling.

In the case of the other light or heavy fractions from the density separation of other types of plastics, energy recovery is usually the only solution because of the heterogeneous composition (various types of plastics or non-plastic materials).

Operational implementation assessment

Table 7-5: Assessment of the removable packaging components criterion

Aspect	Explanation
Technical information requirement for the assessment	<p>Description of packaging materials and packaging aids (including adhesives), in particular with regard to</p> <ul style="list-style-type: none"> • Materials used (including composition and shares), shares of mass, structure • Solubility of the adhesives used • Density of the materials used, melting point and/or glass transition temperature <p>through examinations or on the basis of valid secondary information</p>
Assessment method, tool	<p>If no valid secondary information (for example, manufacturer's data or processing experience on incompatibilities of aggregates, for example, non-removable shares with the target material) is available on the packaging materials, studies on the solubility, density and remelting behaviour on a laboratory scale are helpful:</p> <p>Assessment of the solubility of adhesives / labels: The procedure taken could, for example, be equivalent to the Quick Test QT504 of the European PET Bottle Platform (www.epbp.org/page/8/downloads). The description of the experiment applies to PET. For the other plastic fractions, the procedure can be carried out in an aqueous phase in the respective temperature ranges indicated along the same lines as the procedure described in Quick Test QT504.</p> <p>Assessment of swim and sink behaviour: The procedure taken could, for example, be equivalent to the Quick Test QT502 of the European PET Bottle Platform. Alternatively, a density determination of packaging components after crushing (only non-foamed materials) can be carried out according to DIN 1183-1.</p>

7.3.2 Does the packaging introduce (non-separable) impurities with the risk of contaminating the recycled product or disrupting the recycling process? (Impurities with risks)

Explanation

Impurities with a relatively low risk

During the production of recycled paper, depending on the target product, visual in-homogeneities are to be avoided. No impurities should be introduced into the product which could be perceived as dirt specks or other visual discrepancies in the paper web.

Moreover, components that are sticky, fragmented into small components and can clump together again (stickies) are also unwanted. Larger stickies (over 2 mm in equivalent circular diameter) can be separated using the stock preparation processes. Smaller stickies, however, can lead to deposits on the components of the paper web guiding machine, which cause paper web breaks and production downtimes.

Impurities with a significant risk

Impurities with a significant risk of negatively affecting the paper fibres are all substances that render the paper fibres unusable for reuse. These include wet strength and non-soluble dispersing adhesives.

The European Printing Ink Association (EuPIA) has issued a list³¹ of excluded substances and materials that should no longer be used due to their harmful nature. Components on the EUPIA list are not to be expected in packaging. A general examination can be dispensed with.

During the use of wet strength agents, impregnating agents, waxes, etc. as well as paper and cardboard coated on both sides or metallised (except for liquid packaging board) as well as fibre-based composite packaging and PBC-packaging for non-dry contents, e.g. for liquids, certain foodstuffs, oils and emulsions in general it is necessary to determine the recyclability, according to the PTS method PTS-RH 025/2022 or CEPI/ 4evergreen, for example.

The following overview summarises impurities with a potentially low or significant risk for the production of recycled fibres.

³¹ EuPIA Exclusion List for Printing Inks and related Products

Table 7-11: Overview of contamination with potential risk for reference application Corrugated base paper

	Low risk	Not recyclable [ZSVR 2024]
PBC, PBC-composite and LPB	<p>Limited recyclability due to optical inhomogeneity in the processed material (assessment according to CEPI / 4evergreen scorecard: minor or some visual quality issues)</p> <ul style="list-style-type: none"> The product is recyclable, but could be improved in terms of product design due to its low fibre content (evaluation according to PTS method PTS-RH 025/2022) 	<p>Polymeric thermoplastic dispersion coatings and hot melt adhesive applications, unless it is proven that they do not cause incompatibilities in the recycle. The exceptions for hot melt adhesive applications³² mentioned in the EPRC scorecard apply:</p> <ul style="list-style-type: none"> Adhesive Softening Temperature (according to R&B): ≥ 68 °C Layer thickness (non-reactive adhesive): ≥ 120 μm Layer thickness (reactive adhesive): ≥ 60 μm Horizontal dimensions of adhesive application (in each direction): ≥ 1.6 mm <p>Significant restrictions due to adhesive impurities (assessment according to CEPI / 4evergreen scorecard: "significant adhesion issues")</p> <ul style="list-style-type: none"> Not useful in paper recycling due to insufficient repulpability (evaluation according to PTS method PTS-RH 025/2022) <p>Plastic/Al proportions in LPB: PA coatings (for possible references, see Table 7-7) PET in combination with PE Biodegradable polymers Non-polymer coatings (except aluminum foil coating and SiOx/AlOx/metallisation); Non-PO plastics with a density < 1 g/cm³</p>
	<p>High risk</p> <ul style="list-style-type: none"> Significant visual quality issues (CEPI / 4evergreen scorecard „significant visual quality issues“) 	

³² www.paperforrecycling.eu/download/882.

Operational Execution Evaluation

Table 7-12: Assessment of the criterion "Impurities with risks"

Aspect	Explanation
Technical information requirement for the assessment	Potential recycling incompatibilities in the packaging
Assessment method, tool	Examination according to method PTS-RH 025/2022 or CEPI / 4ever-green <ul style="list-style-type: none"> • Determination of the pulping behaviour and share of unwanted materials (incl. substances which pass into the aqueous phase) • Examination for adhesive impurities or optical inhomogeneities

Valuation analogous Table 7-9.

7.4 Tinplate and non-ferrous metals

7.4.1 Does the packaging contain non-recyclable shares that can be separated during the preparation steps? (separable packaging components)

Explanation

In the case of TP packaging, the material cycle for the iron content of the packaging is almost completely closed during the recycling process. However, losses of non-ferrous metals or organic compounds, for example, occur due to the preparation method (melting process). Specifically, these packaging components are labels, coatings with tin (tinplate), an enamel layer, or other inorganic and organic materials³³.

During the recycling of aluminium packaging, the share of organic components (paper or plastic labels) must be deducted from the recyclability, as these are pyrolyzed.

Table 7-13: Overview of removable, unwanted packaging components

	Non-material components whose separation takes place in the melting or pyrolysis process
Tinplate	Aluminium, silicon, organic packaging components (plastic, PBC)
Aluminium	Organic packaging components (plastic, PBC)

³³ These are oxidised as losses during melting in the blast furnace or the oxygen converter, and the metallic compounds are then separated out via the slag.

Operational Execution Evaluation

Table 7-14: Evaluation of the 'detachable packaging components' criterion

Aspect	Explanation
Technical information requirement for the assessment	Description of packaging materials and all packaging aids, in particular with regard to <ul style="list-style-type: none"> Materials used (including composition and shares), shares of mass, structure through examinations or on the basis of valid secondary information
Assessment method, tool	Dismantling of the packaging and possible determination of the annealing loss (DIN 15169). Expert assessment based on packaging information and/or packaging analysis

Valuation analogous Explanation

During the preparation of standard packaging plastics, there are individual packaging components that are foreign to the material and interfere in the preparation process or can have a negative impact on the quality of the recycled product. However, some of these non-recyclable packaging shares can usually be removed in the various steps of the preparation process (washing, float and sink separation, melt extrusion).

- The washing usually takes place in aqueous medium. The purpose of the washing is to clean product of adhesions and to remove or detach labels, foreign materials and other unwanted components such as prints.
- Subsequently, a density separation (float and sink separation) of the previously crushed and washed packaging is usually carried out so that the requisite plastic fraction can be enriched further. With the use of water, plastic types with a density greater or less than 1 g/cm³ are separated from each other. During the preparation of polyolefins (density < 1 g/cm³), plastics and other materials with a density > 1 g/cm³ can be removed as a sink fraction. Density separation reaches its limits for plastic types with small density differences. Plastics with a similar density such as PP and PE, for example, cannot be separated from each other. In this case, special liquids with a density which is between those of the target plastics can be used. However, this is rarely practised. During the recycling of PET (> 1 g/cm³), float and sink separation can be used to separate and recycle closures in particular, which are mostly made of PE-HD. The crushed components of the closure then end up in the light fraction and are therefore removed from the non-floating PET. PS (> 1 g/cm³) is also obtained as a sinking fraction and freed from specifically lighter PO shares. Changing the density of the original packaging material through the use of blends and additive compounds, for instance, can result in the introduction of impurities into the target fraction of the separation step or lead to the rejection of types of plastic from the target fraction that are actually wanted.
- During the further preparation of plastic fractions, the focus is on obtaining re-granulates (without additives) or regenerates (with additives) in the remelting process. During the extrusion / melting process, the shares that have a lower melting temperature compared with the processing temperature are also transferred into the re-granulate. These can cause a deterioration in the characteristics of the product (see Section 7.2.2). Therefore, the processing of composite materials, blends and plastics with additive compounds is potentially problematic. Although higher melting components can be separated and discharged as residues with the use of melt filtration, they increase the cleaning workload for the filter screen and also lead to yield losses of the target material during the course of the filtration.

Low-melting components, on the other hand, find their way into the recycle and/or decompose beforehand, which leads to a deterioration of the mechanical and visual characteristics of the recycle.

The following is an overview of substances that can be removed during the course of the aforementioned preparation steps.

Table 7-4: Overview of removable, non-recyclable packaging components (according to the European PET Bottle Platform and Plastics Recyclers Europe). Processing temperatures for new goods according to Saechtling.

	Washing of the crushed packaging components	Density separation of the crushed, washed packaging components	Remelting process of the target fraction from the density separation
PE-HD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 160-220°C)
PE-LD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 180-250°C)
PP	Adhesives (water-soluble below 80°C, paper labels)	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 200-270°C)
PET, transparent bottles	Adhesives (water- or alkali-soluble in the temperature range 60 – 80°C), Paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 260-300°C)
PS	Adhesives (water soluble), paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS and with a density >1.08 g/cm ³ : PET, Al	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 170-280°C)

The PO shares of transparent PET bottles (especially caps) can be removed for further recycling during the course of the PET preparation (floating fraction of the density separation). Accordingly, further recycling can also be assumed for rigid PE and PP shares that are separated during PS recycling.

In the case of the other light or heavy fractions from the density separation of other types of plastics, energy recovery is usually the only solution because of the heterogeneous composition (various types of plastics or non-plastic materials).

Operational implementation assessment

Table 7-5: Assessment of the removable packaging components criterion

Aspect	Explanation
Technical information requirement for the assessment	<p>Description of packaging materials and packaging aids (including adhesives), in particular with regard to</p> <ul style="list-style-type: none"> • Materials used (including composition and shares), shares of mass, structure • Solubility of the adhesives used • Density of the materials used, melting point and/or glass transition temperature <p>through examinations or on the basis of valid secondary information</p>
Assessment method, tool	<p>If no valid secondary information (for example, manufacturer's data or processing experience on incompatibilities of aggregates, for example, non-removable shares with the target material) is available on the packaging materials, studies on the solubility, density and remelting behaviour on a laboratory scale are helpful:</p> <p>Assessment of the solubility of adhesives / labels: The procedure taken could, for example, be equivalent to the Quick Test QT504 of the European PET Bottle Platform (www.epbp.org/page/8/downloads). The description of the experiment applies to PET. For the other plastic fractions, the procedure can be carried out in an aqueous phase in the respective temperature ranges indicated along the same lines as the procedure described in Quick Test QT504.</p> <p>Assessment of swim and sink behaviour: The procedure taken could, for example, be equivalent to the Quick Test QT502 of the European PET Bottle Platform. Alternatively, a density determination of packaging components after crushing (only non-foamed materials) can be carried out according to DIN 1183-1.</p>

7.4.2 Does the packaging introduce (non-separable) impurities with the risk of contaminating the recycled product and/or disrupting the recycling process? (Impurities with risks)

Explanation

Explanation

Impurities with a low risk

The type and share of unwanted packaging components depend on the area of application of the recycled product.

In principle, Fe packaging can contain inorganic packaging components such as copper, which forms an alloy with iron in the preparation process. The concentration of the alloy components and the subsequent intended use require either an addition or dilution of the melt by metallic elements that are required in each case.

During the recycling of aluminium beverage cans, even low concentrations of copper (0.2 mass %) and silicon (0.3 mass %) are to be considered as unwanted. During the recycling of other aluminium packaging, higher tolerance limits (copper: 2.5 mass %; silicon: 1 mass %) apply. Here, too, pure aluminium is added until the required alloy is obtained [Erdmann et al., 2009].

Table 7-15: Overview of impurities with risk

	Impurities with a low risk of contamination of the product
Tinplate	Copper
Aluminium	Iron, silicon, copper

Operational Execution Evaluation

Table 7-16: Assessment of the Contamination with Risk criterion

Aspect	Explanation
Technical information requirement for the assessment	<p>Potential contamination (see Explanation Impurities with a low risk)</p> <p>The type and share of unwanted packaging components depend on the area of application of the recycled product.</p> <p>In principle, Fe packaging can contain inorganic packaging components such as copper, which forms an alloy with iron in the preparation process. The concentration of the alloy components and the subsequent intended use require either an addition or dilution of the melt by metallic elements that are required in each case.</p> <p>During the recycling of aluminium beverage cans, even low concentrations of copper (0.2 mass %) and silicon (0.3 mass %) are to be considered as unwanted. During the recycling of other aluminium packaging, higher tolerance limits (copper: 2.5 mass %; silicon: 1 mass %) apply. Here, too, pure aluminium is added until the required alloy is obtained [Erdmann et al., 2009].</p> <p>Table 7-15) in the packaging</p>
Assessment method, tool	Expert assessment based on packaging information or packaging analysis

Valuation analogous Table 7-9.

7.5 Container glass

7.5.1 Does the packaging contain non-recyclable shares that can be separated during the preparation steps? (separable packaging components)

Explanation

In the case of container glass packaging, the material cycle for the glass content of the packaging is almost completely closed during the preparation process. During the preparation process, non-material packaging aids (e.g. labels) are removed which, with the exception of metallic closures, are not recycled mechanically. Furthermore, specific packaging design can reduce the recyclable glass share partially or completely.

Table 7-17: Overview of removable, unwanted packaging components

	Non-material components that are removed during preparation
Container glass	Packaging aids such as closures, labels For removable metallic components such as from closures, a mechanical recycling may be assumed

Table 7-18: Overview of interfering packaging components reducing the recyclable glass share

	Non-material components which reduce recyclable glass share
Container glass	In the case of glass packaging with adhesive labels made from plastic, the glass share covered by these labels cannot be classified as recyclable content if the adhesive labels are waterproof/hydrophobic. Glass components that fall below an optical transmittance of 10%, e.g. due to coating or colouring. With demijohns, i.e. bottles covered with a basket, the glass share is to be considered completely lost.

Operational Execution Evaluation

Table 7-19: Evaluation of the separable packaging component criterion

Aspect	Explanation
Technical information requirement for the assessment	Description of packaging materials and all packaging aids, in particular with regard to <ul style="list-style-type: none"> Materials used (including composition and shares), shares of mass, structure through examinations or on the basis of valid secondary information
Assessment method, tool	Dismantling of the packaging and possible determination of the annealing loss (DIN 15169) Expert assessment based on packaging information and/or packaging analysis

Valuation analogous Explanation

During the preparation of standard packaging plastics, there are individual packaging components that are foreign to the material and interfere in the preparation process or can have a negative impact on the quality of the recycled product. However, some of these non-recyclable packaging shares can usually be removed in the various steps of the preparation process (washing, float and sink separation, melt extrusion).

- The washing usually takes place in aqueous medium. The purpose of the washing is to clean product of adhesions and to remove or detach labels, foreign materials and other unwanted components such as prints.
- Subsequently, a density separation (float and sink separation) of the previously crushed and washed packaging is usually carried out so that the requisite plastic fraction can be enriched further. With the use of water, plastic types with a density greater or less than 1 g/cm³ are separated from each other. During the preparation of polyolefins (density < 1 g/cm³), plastics and other materials with a density > 1 g/cm³ can be removed as a sink fraction. Density separation reaches its limits for plastic types with small density differences. Plastics with a similar density such as PP and PE, for example, cannot be separated from each other. In this case, special liquids with a density which is between those of

the target plastics can be used. However, this is rarely practised. During the recycling of PET (> 1 g/cm³), float and sink separation can be used to separate and recycle closures in particular, which are mostly made of PE-HD. The crushed components of the closure then end up in the light fraction and are therefore removed from the non-floating PET. PS (> 1 g/cm³) is also obtained as a sinking fraction and freed from specifically lighter PO shares. Changing the density of the original packaging material through the use of blends and additive compounds, for instance, can result in the introduction of impurities into the target fraction of the separation step or lead to the rejection of types of plastic from the target fraction that are actually wanted.

- During the further preparation of plastic fractions, the focus is on obtaining re-granulates (without additives) or regenerates (with additives) in the remelting process. During the extrusion / melting process, the shares that have a lower melting temperature compared with the processing temperature are also transferred into the re-granulate. These can cause a deterioration in the characteristics of the product (see Section 7.2.2). Therefore, the processing of composite materials, blends and plastics with additive compounds is potentially problematic. Although higher melting components can be separated and discharged as residues with the use of melt filtration, they increase the cleaning workload for the filter screen and also lead to yield losses of the target material during the course of the filtration. Low-melting components, on the other hand, find their way into the recyclate and/or decompose beforehand, which leads to a deterioration of the mechanical and visual characteristics of the recyclate.

The following is an overview of substances that can be removed during the course of the aforementioned preparation steps.

Table 7-4: Overview of removable, non-recyclable packaging components (according to the European PET Bottle Platform and Plastics Recyclers Europe). Processing temperatures for new goods according to Saechtling.

Washing of the crushed packaging components	Density separation of the crushed, washed packaging components	Remelting process of the target fraction from the density separation
---	--	--

PE-HD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 160-220°C)
PE-LD	Adhesives (water soluble below 60°C), paper labels	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 180-250°C)
PP	Adhesives (water-soluble below 80°C, paper labels)	Packaging components, substances with a density >1 g/cm ³ : PS, PET, PVC, EVA with aluminium	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 200-270°C)
PET, transparent bottles	Adhesives (water- or alkali-soluble in the temperature range 60 – 80°C), Paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 260-300°C)
PS	Adhesives (water soluble), paper labels	Packaging components, substances with a density <1 g/cm ³ : PE, PP, foamed PET, OPP, EPS and with a density >1.08 g/cm ³ : PET, Al	Packaging components, substances, etc. with a melting temperature higher than the processing temperature (approx. 170-280°C)

The PO shares of transparent PET bottles (especially caps) can be removed for further recycling during the course of the PET preparation (floating fraction of the density separation). Accordingly, further recycling can also be assumed for rigid PE and PP shares that are separated during PS recycling.

In the case of the other light or heavy fractions from the density separation of other types of plastics, energy recovery is usually the only solution because of the heterogeneous composition (various types of plastics or non-plastic materials).

Operational implementation assessment

Table 7-5: Assessment of the removable packaging components criterion

Aspect	Explanation
Technical information requirement for the assessment	<p>Description of packaging materials and packaging aids (including adhesives), in particular with regard to</p> <ul style="list-style-type: none"> • Materials used (including composition and shares), shares of mass, structure • Solubility of the adhesives used • Density of the materials used, melting point and/or glass transition temperature <p>through examinations or on the basis of valid secondary information</p>
Assessment method, tool	<p>If no valid secondary information (for example, manufacturer's data or processing experience on incompatibilities of aggregates, for example, non-removable shares with the target material) is available on the packaging materials, studies on the solubility, density and remelting behaviour on a laboratory scale are helpful:</p> <p>Assessment of the solubility of adhesives / labels: The procedure taken could, for example, be equivalent to the Quick Test QT504 of the European PET Bottle Platform (www.epbp.org/page/8/downloads). The description of the experiment applies to PET. For the other plastic fractions, the procedure can be carried out in an aqueous phase in the respective temperature ranges indicated along the same lines as the procedure described in Quick Test QT504.</p> <p>Assessment of swim and sink behaviour: The procedure taken could, for example, be equivalent to the Quick Test QT502 of the European PET Bottle Platform. Alternatively, a density determination of packaging components after crushing (only non-foamed materials) can be carried out according to DIN 1183-1.</p>

7.5.2 Does the packaging introduce (non-separable) impurities with the risk of contaminating the recycled product and/or disrupting the recycling process? (Impurities with risks)

Explanation

Impurities with a significant risk

In the case of container glass, the introduction of lead oxide must be prevented, as the visual characteristics of the fragments and/or the new glass product are changed. Borosilicate glass interferes with the recycling of container glass because boron and aluminium oxides change the properties of normal glass. However, these glasses are not used in the field of container glass and/or are mainly used in the chemical industry. Metals such as lead, tin and iron (wrappings on champagne and wine bottles) have a corrosive effect on the melting tanks. Even very low concentrations of chrome iron, cobalt and copper can lead to a discolouration of the molten glass.

During the recycling of container glass, any inclusions in the glass (brackets for fixing the lid) or applications on the glass made of metal that cannot be removed by breaking are also problematic, as these get into the molten glass. There, they form inclusions in the glass, which can weaken the glass structure and lead to breakage. Aluminium caps (screw caps) that get into

the molten glass lead to the formation of silicon that forms inclusions that weaken the glass structure. Ceramics, porcelain and earthenware do not dissolve in the melt. Inclusions form, which lead to breakage due to stresses in the glass.

Crystal glass packaging containing lead is not recyclable [ZSVR 2024].

The following overview summarises the possible impurities in container glass recycling.

Table 7-20: Overview of contamination with risk

	Not recyclable [ZSVR 2024]
Container glass	<ul style="list-style-type: none"> Lead glass Borosilicate glass Container glass with ceramic components Container glass with metal nets Swing-top closures with exclusively non-ferromagnetic metal parts

Operational Execution Evaluation

Table 7-21: Assessment of the criterion "Impurities with risks"

Aspect	Explanation
<p>Technical information requirement for the assessment</p>	<p>Potential contamination (see Does the packaging introduce (non-separable) impurities with the risk of contaminating the recycled product and/or disrupting the recycling process? (Impurities with risks))</p> <p>Explanation</p> <p>Impurities with a significant risk</p> <p>In the case of container glass, the introduction of lead oxide must be prevented, as the visual characteristics of the fragments and/or the new glass product are changed. Borosilicate glass interferes with the recycling of container glass because boron and aluminium oxides change the properties of normal glass. However, these glasses are not used in the field of container glass and/or are mainly used in the chemical industry. Metals such as lead, tin and iron (wrappings on champagne and wine bottles) have a corrosive effect on the melting tanks. Even very low concentrations of chrome iron, cobalt and copper can lead to a discolouration of the molten glass.</p> <p>During the recycling of container glass, any inclusions in the glass (brackets for fixing the lid) or applications on the glass made of metal that cannot be removed by breaking are also problematic, as these get into the molten glass. There, they form inclusions in the glass, which can weaken the glass structure and lead to breakage. Aluminium caps (screw caps) that get into the molten glass lead to the formation of silicon that forms inclusions that weaken the glass structure. Ceramics, porcelain and earthenware do not dissolve in the melt. Inclusions form, which lead to breakage due to stresses in the glass.</p> <p>Crystal glass packaging containing lead is not recyclable [ZSVR 2024].</p> <p>The following overview summarises the possible impurities in container glass recycling.</p> <p>Table 7-20) in the packaging</p>
<p>Assessment method, tool</p>	<p>Expert assessment based on packaging information or packaging analysis</p>

Valuation analogous Table 7-9.

8 Quantitative recyclability assessment

The quantitative assessment of the recyclability of packaging is carried out in the framework of a scoring model using scoring points. The starting point for the assessment are the criteria for assessing the recyclability (Sections 5 to 0). A percentage weighting is specified for the assessment criteria in the framework of the scoring model (see The recyclability of the packaging is therefore measured according to the number of scoring points achieved. It should be noted that the scoring points and/or their % share of the maximum score do not allow for the conclusion to be drawn as to what percentage mass share of the original packaging could actually be available as a secondary product after the recycling. If the assessment is 0 points (level 5) for one criterion, the assessment of the other criteria and the determination of recyclability continues as described. On the other hand, if a criterion is assessed at KO in level 5, it must be assumed that the packaging is not recyclable and must therefore be assessed as non-recyclable. To allow for the identification of potentials for the improved recyclability for packaging of this kind in particular, a conditional assessment is made for the assessment levels to which the KO criterion is not allocated.

Packaging made of glass, PBC and TP receives the best overall assessment for the minimum size criterion,

- a packaging made of glass and PBC is collected on a material-specific basis and thus a LWP sorting process, to which the criterion of minimum size refers, is not intended and/or
- an identification of small TP packaging from the LWP mixture is also assumed.
- Packaging whose TP and/or the small AI share is not sufficient for unrestricted identification on the basis of magnetising capacity or conductivity, the sorting behaviour of the packaging is assessed on the basis of the material with the greatest weight share (for example, plastic or paper) (also see Table 6-4)

For packaging that contains separable components (see Chapter 4 for definition), separate recyclability assessments are required for each component, as the components may be sent to different sorting and processing routes.

The calculation methodology is shown in the following table using the assessment of two pieces of packaging as an example.

Table 8-2), which is determined independently of the consideration of an individual piece of packaging.

The quantitative recyclability assessment is carried out in the following steps

- Based on the explanations in the Sections 5 to 7, the degree of fulfilment for the individual assessment criteria can initially be assessed qualitatively for the packaging to be examined.
- Based on the qualitative assessment of the degree of fulfilment of the packaging to be examined, a graded quantitative assessment (grading) between 20 (best assessment – level 1) and 0 or KO (worst assessment – level 5) is carried out for each assessment criterion. The underlying scaling is shown in Table 8-1.
- Multiplying the criteria-specific assessment of the packaging by the corresponding weighting for the respective criterion results in an individual scoring for each criterion.
- By adding up all the individual scores, the overall score for recyclability is obtained.

Table 8-1: Scoring model for the quantitative evaluation of recyclability

Kriterium	Skalierung (Bewertung in Punkten)				
	Stufe 1	Stufe 2	Stufe 3	Stufe 4	Stufe 5
	20	15	10	5	0
					KO
Ebene 1: Zuordnung der Verpackung zum Erfassungssystem					
Erfassungssystem zuordenbar	Erfassungssystem für Verbraucher intuitiv problemlos zuordenbar	Erfassungssystem für Verbraucher intuitiv eingeschränkt zuordenbar	-	Erfassungssystem für Verbraucher intuitiv schwer zuordenbar	Erfassungssystem für Verbraucher nicht zuordenbar
Ebene 2: Sortierbarkeit gemischt erfasster Verpackungen (LVP)					
Mindestgröße	Vp hat eine ausreichende Größe (deutlich >20mm)	-	-	Vp hat keine ausreichende Größe (deutlich <20mm)	-
Identifizier- / Abtrennbarkeit	WB kann uneingeschränkt sortiert und abgetrennt werden	-	-	-	-
Aluminium (Leitfähigkeit)	Al kann uneingeschränkt sortiert/abgetrennt werden	-	-	-	-
KS, FKN, PPK-Verbund, PPK, Glas (Oberflächeneigenschaft)	Detektion/Abtrennung Zielmaterial uneingeschränkt möglich, oder Sonderfall formflexibler	Detektion/Abtrennung Zielmaterial eingeschränkt	Detektion/Abtrennung Zielmaterial deutlich eingeschränkt	-	Detektion/Abtrennung Zielmaterial nicht möglich
Ebene 3: Eignung für werkstoffliche Verwertung und Bereitstellen von Sekundärprodukten					
Hochwertigkeit Verwertungsweg	Erwarteter Verwertungsweg ist hochwertig werkstofflich	Erwarteter Aufbereitungsweg ist überwiegend hochwertig werkstofflich	Erwarteter Aufbereitungsweg ist nur zum Teil hochwertig werkstofflich	-	Erwarteter Verwertungsweg Zielmaterial ausschließlich energetisch bzw. nur im Einzelfall hochwertig werkstofflich
Abtrennbare, nicht verwertbare Anteile	Vp enthält keine abtrennbaren, nicht-verwertbaren Anteile	Vp enthält geringe Anteile (< 10 Massen-%)	Vp enthält signifikante Anteile (> 10 Massen-% und < 30 %)	Vp enthält erhebliche Anteile (> 30 und <50 Massen-%)	Vp wird vollständig aus der Zielfraktion abgetrennt
Nicht abtrennbare Anteile bzw. Verunreinigungen	Vp trägt keine störenden Verunreinigungen ein	Vp trägt eine oder zwei unterschiedliche Art/en an Verunreinigung mit geringem Kontaminationsrisiko ein	Vp trägt drei oder mehr unterschiedliche Arten an Verunreinigungen mit geringem Kontaminationsrisiko ein	Vp trägt eine oder zwei unterschiedliche Art/en an Verunreinigung mit hohem Kontaminationsrisiko ein	Vp trägt störende Verunreinigungen ein, die eine Recyclingfähigkeit ausschließen

The recyclability of the packaging is therefore measured according to the number of scoring points achieved. It should be noted that the scoring points and/or their % share of the maximum score do not allow for the conclusion to be drawn as to what percentage mass share of the original packaging could actually be available as a secondary product after the recycling. If the assessment is 0 points (level 5) for one criterion, the assessment of the other criteria and the determination of recyclability continues as described. On the other hand, if a criterion is assessed at KO in level 5, it must be assumed that the packaging is not recyclable and must therefore be assessed as non-recyclable. To allow for the identification of potentials for the improved recyclability for packaging of this kind in particular, a conditional assessment is made for the assessment levels to which the KO criterion is not allocated.

Packaging made of glass, PBC and TP receives the best overall assessment for the minimum size criterion,

- a packaging made of glass and PBC is collected on a material-specific basis and thus a LWP sorting process, to which the criterion of minimum size refers, is not intended and/or
- an identification of small TP packaging from the LWP mixture is also assumed.

- Packaging whose TP and/or the small AI share is not sufficient for unrestricted identification on the basis of magnetising capacity or conductivity, the sorting behaviour of the packaging is assessed on the basis of the material with the greatest weight share (for example, plastic or paper) (also see Table 6-4)

For packaging that contains separable components (see Chapter 4 for definition), separate recyclability assessments are required for each component, as the components may be sent to different sorting and processing routes.

The calculation methodology is shown in the following table using the assessment of two pieces of packaging as an example.

Table 8-2: Scoring model for quantitative evaluation of recyclability based on fictitious packaging examples

Criteria	A: Criteria in [%] Total = 100%	Packaging I		Packaging II	
		B: Assessment (0 bis 20)	A*B: Scoring-points	B: Assessment (0 bis 20)	A*B: Scoring-points
Stage 1: Allocation of packaging to the correct disposal system					
Collection matchable	10%	20	2	20	2
Level 2: Sorting capacity of mixed packaging (LWP) collected					
Minimum size	10%	20	2	20	2
Identifiability	20%				
Tinplate (Magnetisability)		-	-	-	-
Aluminium (Conductivity)		-	-	-	-
Plastic, LPB, PBC composite, PBC, glas (Surface characteristics)		15	3	15	3
Level 3: Suitability for mechanical recycling and provision of secondary products					
Quality of recycling method	20%	20	4	KO	KO
Separable parts that cannot be recycled	20%	15	3	-	-
Non-separable components, impurities	20%	20	4	-	-
			Bewertung		Assessment
Recyclability in total			18 out of 20		non-recyclable
Recyclability level 1			2 out of 2		(2 out of 2)
Recyclability level 2			5 out of 6		(5 out of 6)
Recyclability level 3			11 out of 12		KO

The further classification of recyclability based on the determined scoring points is shown in the following table.

Table 8-3: Classification of recyclability based on the scoring model

Scoring points	% share lower limit of maximum score (20)	Classification of recyclability
greater than, equal to 19	95%	Very good
less than 19 and greater than or equal to 16	80%	Good
less than 16 and greater than or equal to 13	65%	Limited
less than 13 and greater than or equal to 10	50%	Considerably limited
less than 10	<50%	Poor
KO assessment in one criterion		Non-recyclable

Literature

- [APR 2021]: APR Design Guide for Plastics Recyclability. The Association of Plastics Recyclers. <https://plasticsrecycling.org/apr-design-guide> (berücksichtigt mit Stand vom 12.09.2024)
- [Bosewitz, 2013]: Bosewitz, S. [Hrsg.]: Kunststoffrecycling in Produkten – Herkunftskatalog von Erzeugnissen aus Kunststoffabfallströmen, 1. Auflage, VGE Verlag GmbH, Essen, 2013
- [bvse 2016]: Glasrecycling – ein in sich geschlossener Materialkreislauf. www.bvse.de/342/491/4. abgerufen am 24.02.2016
- [Consultic 2015] Analyse/Beschreibung der derzeitigen Situation der stofflichen und energetischen Verwertung von Kunststoffabfällen in Deutschland. Studie erstellt im Auftrag der Interessengemeinschaft der thermischen Abfallbehandlungsanlagen in Deutschland e.V.
- [Dehoust et al 2012]: Analyse und Fortentwicklung der Verwertungsquoten für Wertstoffe. UBA-Text 40/2012
- [Erdmann et al. 2009]: Einfluss von RFID-Tags auf die Abfallentsorgung. UBA-Text 27/2009.
- [FKN, 2007]: Fachverband Kartonverpackungen für flüssige Nahrungsmittel e.V. (Hrsg.): Getränkekarton – Im Kreislauf der Natur; www.getraenkekarton.de, abgerufen am 05.09.2017
- [GDA, W 18]: GDA - Gesamtverband der Aluminiumindustri e.V. (Hrsg.): Aluminium in der Verpackung – Herstellung, Anwendung, Recycling (Merkblatt W18); Düsseldorf
- [Gruber, 2011]: Gruber, E.: Papier- und Polymerchemie Vorlesungsskriptum zum Lehrgang „Papier-technik“ an der Dualen Hochschule Karlsruhe, <http://www.gruberscript.net>, abgerufen am 12.09.2017
- [Öko-Institut 2016]: Umweltpotenziale der getrennten Erfassung und des Recyclings von Wertstoffen im Dualen System. Ökobilanz für das Duale System Deutschland.
- [Saechtling] Karl Oberbach: Kunststoff-Taschenbuch. 28.Ausgabe Hanser Verlag
- [UBA 2024]: S. Dorn, M. Fabian: Praxis der Sortierung und Verwertung von Verpackungen im Sinne des § 21 VerpackG 2022/2023. Veröffentlicht als Teilbericht zum Vorhaben mit der Forschungskennzahl 3722 34 im Auftrag des Umweltbundesamtes. Dessau-Roßlau, August 2024
- [UBA_2016-1]: Umweltbundesamt (Hrsg.): Umweltbezogene Bilanzierung von „intelligenten“ und „aktiven“ Verpackungen hinsichtlich der Recyclingfähigkeit und Durchführung eines Dialogs mit Akteuren der Entsorgungs- und Herstellungsbranche, Dessau-Roßlau, April 2016
- [ZSVR 2024]: Mindeststandard für die Bemessung der Recyclingfähigkeit von systembeteiligungspflichtigen Verpackungen gemäß § 21 Abs. 3 VerpackG vom September 2024. Stiftung Zentrale Stelle Verpackungsregister